

Effect of Wood Acetylation with Vinyl Acetate and Acetic Anhydride on the Properties of Wood-Plastic Composites

Nilgül Özmen,^a Nihat Sami Çetin,^{a*} Fatih Mengeloğlu,^a Emre Birinci,^b and Kadir Karakuş^a

Chemical modifications of Scots pine (*Pinus sylvestris*) wood flour were performed with vinyl acetate (VA) and acetic anhydride (AA) in the presence of potassium carbonate as a catalyst. Scots pine wood flour samples were successfully acetylated with VA (19 wt% gain) and AA (24 wt% gain). The effect of chemical modification of the Scots pine wood flour with AA and VA on the mechanical properties of wood high-density polyethylene composites (WPC) was determined. It was observed that acetylation of wood flour allowed a significant increase in both the mechanical properties and the thermal stability of the WPCs. It was concluded that acetylation of lignocellulosic fibers improves thermal stability, dispersion in the polymer matrix, and compatibility with the polymer matrix.

Keywords: Acetylation; Acetic anhydrides; Vinyl acetate; Wood plastic composites; Scots pine

Contact information: a: Department of Forest Industry Engineering, Faculty of Forestry, Kahramanmaraş Sütçü İmam University, Kahramanmaraş, Turkey; b: Araç Vocational School of Higher Education, Kastamonu University, Kastamonu, Turkey; *Corresponding author: nihatchetin@yahoo.com

INTRODUCTION

A composite material can be defined as the heterogeneous combination of two or more components to form a filled or reinforced matrix in which the combined effect of the components possesses superior properties compared with the individual components alone (Popa and Breaban 1995). Replacing man-made fiber with a lignocellulosic alternative offers a relatively cheaper and more environmentally friendly alternative material. The most conspicuous problem of using lignocellulosic fiber as reinforcement in a synthetic matrix is the lack of compatibility of the lignocellulosic material with the matrix. Lignocellulosic materials are hydrophilic (abundance of OH functionality), while thermoplastic (or many thermoset) polymers are hydrophobic. As a result of this divergent behavior, the adhesion between plant fibers and polymers can be very poor. The bonding between the reinforcing material and the matrix plays an important role in determining the mechanical properties of a composite material.

Various methods may be employed to improve bond quality or compatibility of lignocellulosic materials with a hydrophobic matrix. Two methods are the use of compatibilizers (silanes, isocyanates, MAPE (maleic anhydride-modified polyethylene, etc.)) and chemical modification of the lignocellulosic material (acetylation, epoxide modification, etc.) (Schneider and Brebner 1985; Maldas *et al.* 1988; 1989; Kokta *et al.* 1989; Karnani *et al.* 1997; Rowell 2006a).

For improving the bond between the matrix and the reinforcing material, coupling agents such as isocyanates and silanes (Raj *et al.* 1989; Maldas *et al.* 1989) or

compatibilizers can be used because compatibilizers possess properties of both the matrix and the reinforcement in one molecule (Maldas *et al.* 1988; 1989; Felix and Gatenholm 1991; Rowell *et al.* 1997; Sanadi *et al.* 1993; 1997; Simonsen *et al.* 1997; Oksman and Clemons 1998; Oksman and Lindberg 1998).

Chemical modification of wood or natural fibers can be defined as a chemical reaction between some reactive part of a wood or fiber component and a single chemical reagent, with or without a catalyst (Rowell 2006b). All of the methods investigated to date have involved the chemical reaction between a reagent and the cell wall polymer hydroxyl groups. A number of reviews of chemical modification of lignocellulosic materials have been published (Banks and Lawther 1994; Kumar 1994; Matsuda 1996; Hon 1996; Rowell 2006a; Hill 2006). Most of the chemical modification reactions are carried out in order to improve the dimensional stability or bio-resistance of wood. Many wood modification reactions have been studied, of which the most useful are those that include reaction with epoxides, anhydrides, or isocyanates (Hon 1996; Rowell 2006b; Çetin 2000; Çetin and Özmen 2001; Çetin *et al.* 2005; Hill 2006; Özmen *et al.* 2007). Maritime pine, Scots pine sapwood, and hemp fibers have recently been successfully acetylated with a new transesterification reaction using vinyl acetate in the presence of various catalysts such as potassium acetate, potassium carbonate, and sodium carbonate (Jebrane and Sebe 2007; Jebrane *et al.* 2011; Çetin *et al.* 2011; Özmen 2012). In the literature, there are some papers dealing with acetic anhydride modified fiber reinforced polymer composites (Tserki *et al.* 2006; Lisperguer *et al.* 2007; Abdul Khalil *et al.* 2007; Luz *et al.* 2008; Mat Taib *et al.* 2010). Some authors claim that acetylation can improve the mechanical and thermal properties of WPCs (Tserki *et al.* 2006; Lisperguer *et al.* 2007; Abdul Khalil *et al.* 2007). In contradiction to these studies, it was also reported that acetylation reduced the mechanical properties of WPCs (Luz *et al.* 2008; Mat Taib *et al.* 2010).

The objective of this study was to determine the mechanical performance of acetylated and unmodified Scots pine wood flour-reinforced high density polyethylene composites. Two different approaches of acetylation (acetic anhydride and vinyl acetate) were evaluated and the results were compared with those of unmodified WPCs.

EXPERIMENTAL

Preparation of Wood Flour

For wood modification, Scots pine (*Pinus sylvestris*) sapwood was ground using a hammer mill and sieved to a size of 250 to 425 μm . Before reaction, the samples were subjected to Soxhlet extraction with deionised water for 6 h, and then with a mixture of toluene/acetone/ethanol (4/1/1, v/v) for 6 h. This was done to remove the extractive materials from the wood. The samples were then oven-dried at $103\pm 2^\circ\text{C}$ and allowed to cool to ambient temperature in a desiccator containing phosphorous pentoxide before determination of weight.

Acetylation of Scots Pine Wood Flour

500 g of the extractive-free Scots pine sapwood flour was transferred to a 2-L glass reactor containing a dimethyl formamide (DMF) solution with acetic anhydride (AA) or vinyl acetate (VA). All reactions were performed with the presence of potassium carbonate (K_2CO_3) as a catalyst at 100°C for 6 h. The acetylation reaction conditions

were derived from an earlier publication (Çetin *et al.* 2011). The treated samples were Soxhlet extracted with deionised water for 6 hours then with the toluene/acetone/ethanol mixture (4/1/1, v/v) for 6 h. This was done to remove excess unreacted chemicals and byproducts. The acetylated Scots pine wood flour was oven-dried overnight at $103\pm 2^\circ\text{C}$, transferred to a desiccator containing phosphorus pentoxide until cool, and then weight gain levels (WPG) were determined according to Equation 1,

$$\text{WPG (\%)} = \frac{W_2 - W_1}{W_1} \times 100 \quad (1)$$

where W_1 is the sample weight before treatment and W_2 is the sample weight after treatment.

Infrared Spectroscopy

Infrared absorption spectra of the acetylated and unmodified wood flour were obtained using the KBr (potassium bromide) technique with a Shimadzu 8400s FT-IR spectrometer. The spectra were collected over the 4000 to 400 cm^{-1} wavenumber range, at a resolution of 4 cm^{-1} (40 scans).

^{13}C CP-MAS NMR Analysis

Solid state ^{13}C CP-MAS (Cross Polarization-Magic Angle Spinning) NMR spectra of acetylated and unmodified Scots pine wood flour were obtained at room temperature using a Bruker DPX-400 NMR spectrometer (Bruker), with MAS rates of 4 and 8 kHz and a frequency of 100.61 MHz for ^{13}C NMR. Acquisition time was 0.07 s. The pulse repetition time was 4 s and the cross polarization contact time was 1.5 s. All the spectra were run for 15 h (25,000 scans).

Thermogravimetric (TGA) Analysis

The thermogravimetric analyses of the control and acetylated wood flour-reinforced HDPE composites were performed using a thermal gravimetric analyzer (Perkin Elmer STA-6000). The sample weight was 20 mg. The measurements were carried out at a heating rate of $20^\circ\text{C}/\text{min}$ in an inert nitrogen atmosphere with a flow rate of 20 mL/min. Weight loss versus temperature were recorded.

Production of Wood-Plastic Composites (WPC)

High-density polyethylene was obtained from Petkim, Turkey (HDPE; Petilen[®] YYS0464). Four different composites were produced: HDPE (neat polymer), W20 (20 wt% extractive free wood flour filled HDPE), AA20 (20 wt% acetic anhydride modified wood flour filled HDPE), and VA20 (20 wt% vinyl acetate modified wood flour filled HDPE). Initially, the wood flour and HDPE were mixed with a high-speed mixer for 10 min then WPC pellets were produced using a single screw extruder. The temperature setting from the hopper to die was 150/170/170/177 $^\circ\text{C}$, and the screw speed was 100 rpm. The pellets were dried at 70 $^\circ\text{C}$ overnight. For injection moulding, the pellets (wood/HDPE ratio of 20/80 by weight) were melted by a single screw HDX-88 Injection Molding Machine (pressure: 100 bar, injection speed: 80 mm/sec; screw speed: 40 rpm). Then the molten material was injected into dumbbell-shaped moulds to produce the

samples for tensile strength testing and into two bar-shape moulds to produce the flexural and impact specimens. After injection, the samples were rapidly cooled.

Mechanical tests were performed in order to determine the mechanical properties of the produced WPCs. Prior to testing, all samples were conditioned at a relative humidity of $65\pm 5\%$ and a temperature of $23\pm 2^\circ\text{C}$ for 7 days. For each WPC group, ten replicates were tested. Tensile specimens (dogbone shape (type III)) were tested with a crosshead speed of 5 mm/min. The flexural specimens (5 mm (t) x 13 mm (w) x 150 mm (l)) were tested in the three-point loading mode with a crosshead speed of 2 mm/min on a Zwick Roell Z010 Universal Testing machine. Notched impact specimens (5 mm (t) x 12.7 mm (w) x 64 mm (l)) were tested on a Zwick HIT5.5P Impact Testing machine. The notches were cut using a Polytest notching cutter by RayRan. The density, tensile, flexural, and impact properties of the manufactured samples were determined in accordance with ASTM D792 (2007), ASTM D638 (2001), ASTM D6109 (2005), and ASTM D256 (2005), respectively.

Scanning Electron Microscope (SEM) Analysis

The WPC bars were dipped in liquid nitrogen and then snapped in two to get fractured surfaces for SEM analysis. The surfaces were analyzed directly with a JEOL scanning electron microscope (Model NeoScope JCM-5000).

Statistical Analysis

Analysis of variance (ANOVA) was used to determine the effect of acetylation on the selected mechanical properties using Design-Expert 7.0.3. The resulting F value was compared to the tabular F value at the 95% probability level. When F tests resulted in significant differences, comparisons between means were made by Tukey test. Statistically different groups ($P < 0.05$) are shown on the graphs with different capital letters.

RESULTS AND DISCUSSION

The reaction mechanism between Scots pine wood flour hydroxyl groups and acetic anhydride (AA) or vinyl acetate (VA) is shown in Fig. 1. In order to compare the classical AA modification with the new VA technique, the same reaction protocols were applied to both methods. The 24% and 19% WPG levels were achieved for 6 hours of reaction with K_2CO_3 -catalyzed acetic anhydride (AA) and vinyl acetate (VA), respectively.

Figure 2 shows the FTIR spectra of AA-modified (24% WPG), VA-modified (19% WPG), and unmodified (W) Scots pine wood flour. As can be seen in Fig. 3, there was no spectral difference observed between the acetic anhydride-modified and vinyl acetate-modified samples. All modified samples showed a strong carbonyl stretching vibration ($\nu_{\text{C=O}}$) peak in the region of 1745 cm^{-1} . Both the AA and VA-modified samples also showed a peak in the region of 1242 cm^{-1} due to the C-O stretching vibration of the acetyl moieties. The esterification reaction was also confirmed by the appearance of a new peak at 1375 cm^{-1} , attributed to the C-H bending ($\delta_{\text{s C-H}}$) vibrations of the methyl groups introduced (Çetin *et al.* 2005, 2011; Özmen 2012).

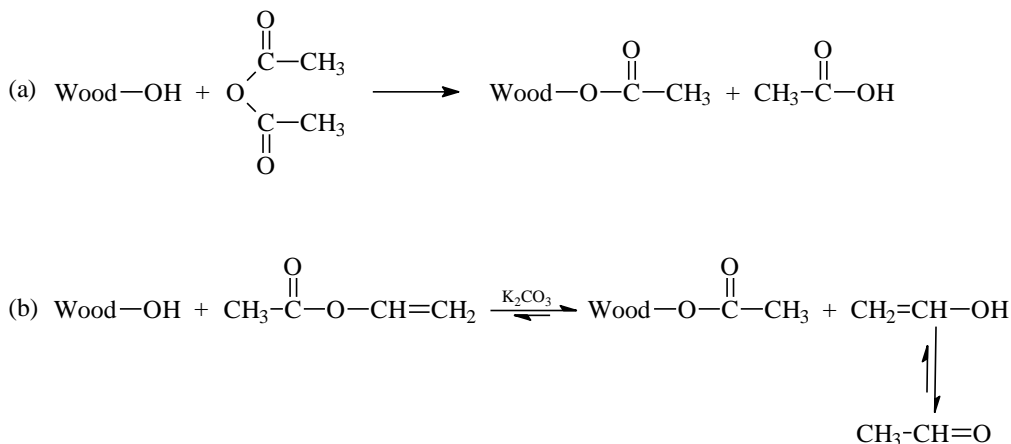


Fig. 1. The reaction of (a) acetic anhydride and (b) vinyl acetate with Scots pine wood flour

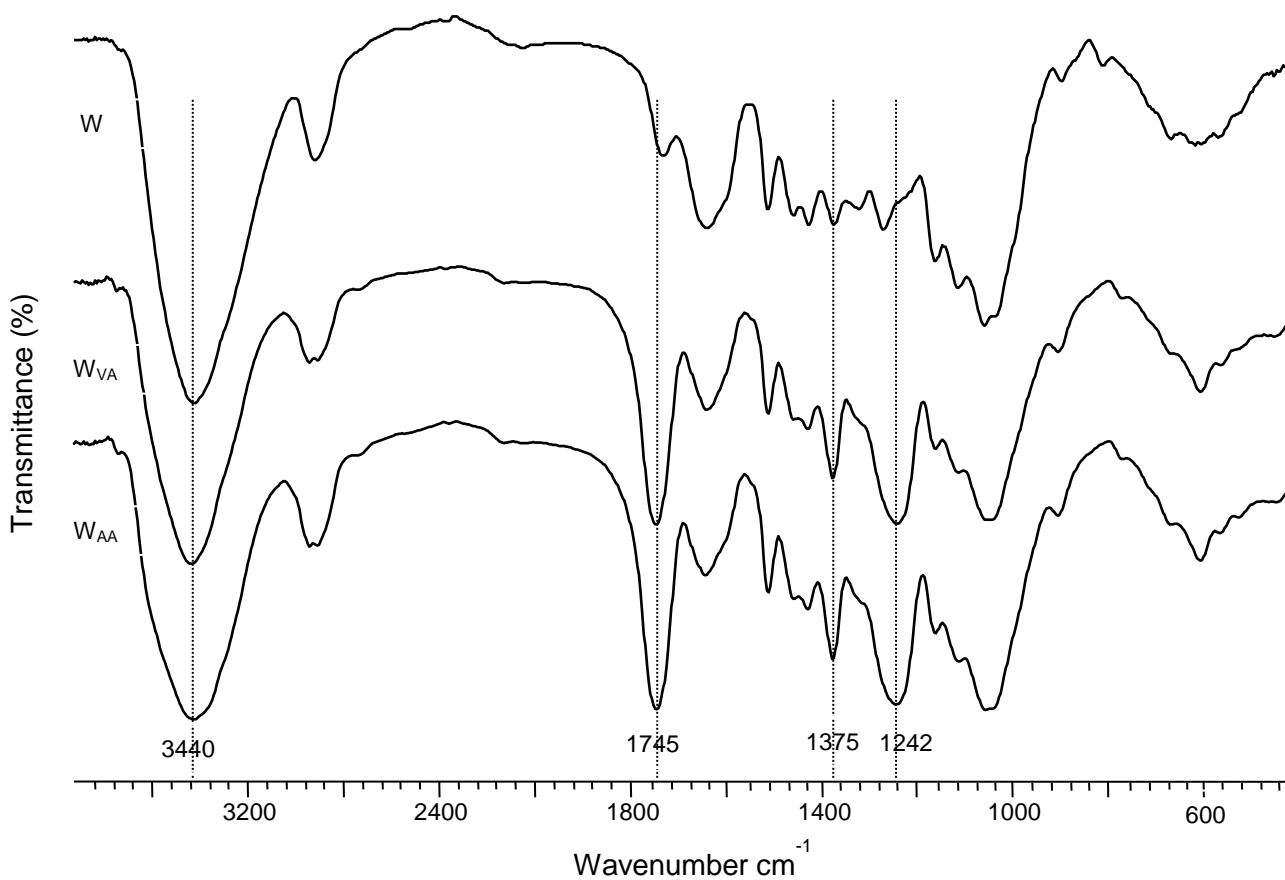


Fig. 2. FTIR spectra of untreated (W), acetic anhydride-modified (24% WPG) (W_{AA}), and vinyl acetate-modified (19% WPG) (W_{VA}) Scots pine wood flour

For further confirmation, the same samples were also characterized using ¹³C CP-MAS NMR. The results are shown in Fig. 3. The carbon atoms of the cellulose component are assigned to the following peaks: C₁ (anomeric C) 105 δ (ppm), C₄ 88 δ (ppm), C_{2,3,5} 71 δ (ppm), and C₆ 65 δ (ppm). Lignin, due to its heterogeneous nature,

produces a broad peak at 150 δ (ppm) (Boonstra *et al.* 1996). The NMR spectra of the AA- and VA-modified wood flour showed new peaks in the 21 δ (ppm) and 170 δ (ppm) regions due to the methyl band and the carboxylic group of the acetyl group, respectively.

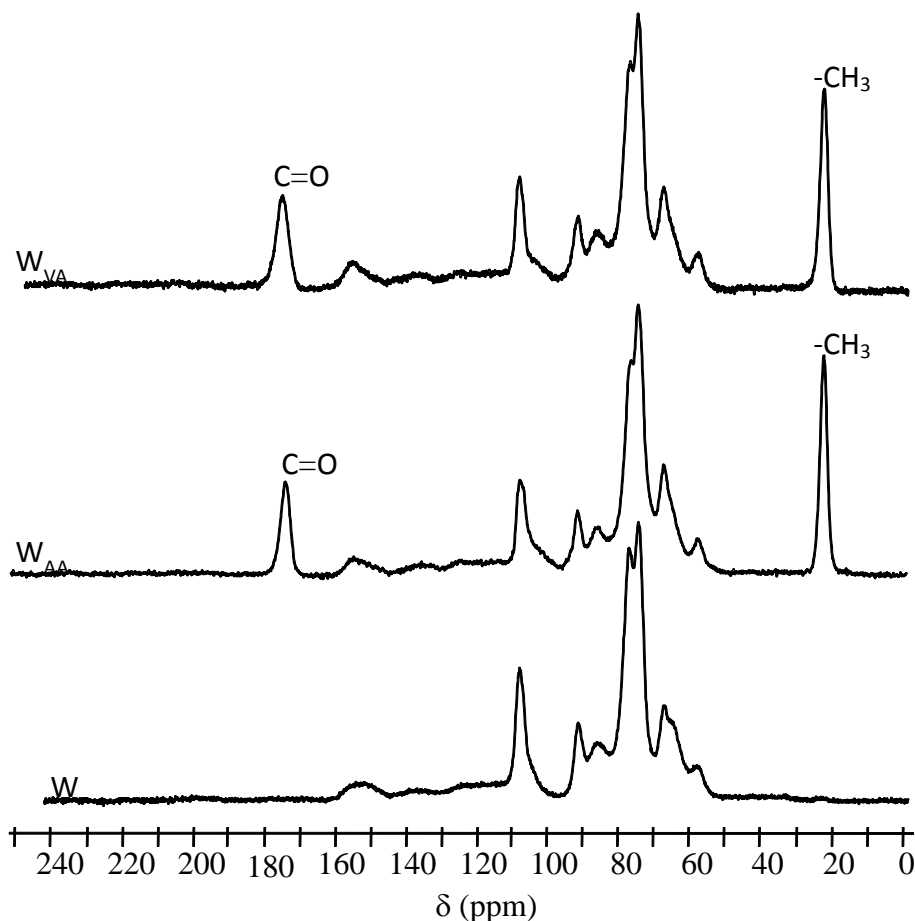


Fig. 3. ¹³C CP-MAS NMR spectra of unmodified (W), acetic anhydride-modified (24% WPG) (W_{AA}), and vinyl acetate-modified (19% WPG) (W_{VA}) Scots pine wood flour

Figure 4 shows the density of the produced WPC groups. Statistical analysis indicated a difference between HDPE and W20. It is believed that the cellular structure of wood partially collapses during injection molding due to the high pressure, which leads to some increase in density. Especially for the injection-molded WPCs, similar results have been reported (Stark *et al.* 2004). It should also be noted that after acetylation of wood flour, the densities of the resulting composites were slightly reduced. The reason for this reduction might be that acetylated wood flour contains less lignocellulosic material than unmodified wood flour at a given weight % loading.

Figure 5 shows the tensile strengths of the HDPE, W20, AA20, and VA20 composites at 20 wt% wood flour loading. It is clear from the figure that the acetylation of Scots pine wood flour had a positive effect on tensile strength. Acetylation substitutes the wood cell wall hydroxyl groups with acetyl groups (see Fig. 1), altering the wood surface in particular, making it more hydrophobic. Since now both AA20 or VA20 and HDPE are hydrophobic, it is predicted that AA20 or VA20 might exhibit better compatibility with HDPE than W20. This would result in an increase in tensile strength of the composites as the fiber–matrix interaction is now possible to facilitate stress transfer from

HDPE to AA20 or VA20. It should also be noted that the addition of extractive-free wood flour to the HDPE polymer matrix did not reduce the tensile strength.

The tensile modulus values of the HDPE, W20, AA20, and VA20 composites at 20 wt% wood flour loading are presented in Fig. 6. The tensile modulus of the HDPE significantly increased with the addition of wood flour. This is usually explained by the rule of mixture (Matuana and Balatinecz 1998; Mengeloglu and Karakus 2008). Wood flours have a higher modulus than polymer matrixes, and as a result, their mixture produces higher modulus values compared to the polymer itself. From the figure, it is also seen that acetylation of Scots pine wood flour with VA did not affect tensile modulus values; however, acetylation of wood flour with AA had a negative effect on the tensile modulus property compared to unmodified wood flour-filled composites (W20).

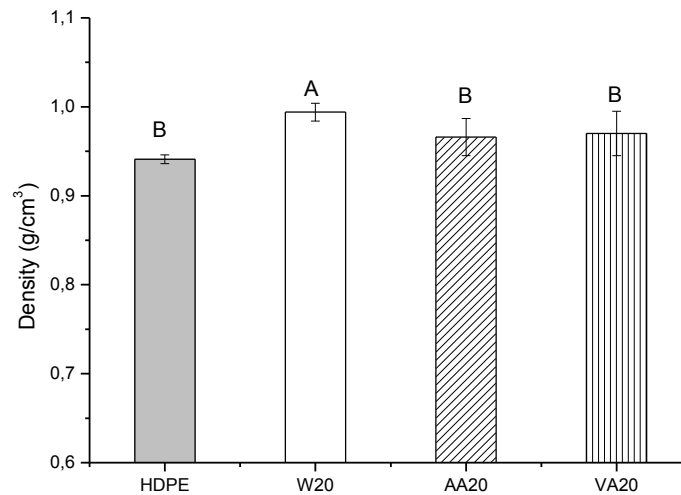


Fig. 4. Density of WPCs

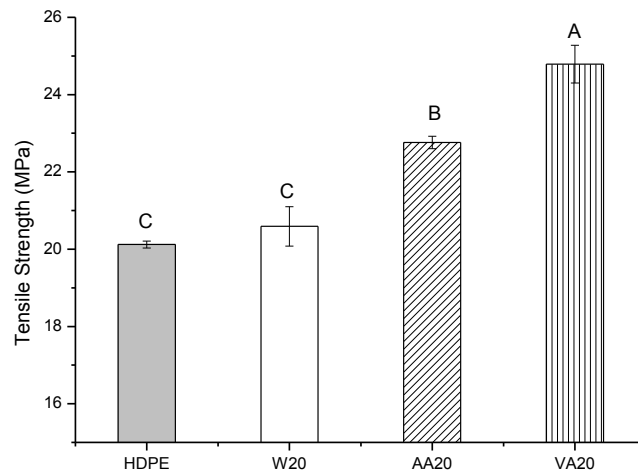


Fig. 5. Effect of acetylation on the tensile strength (TS) values of WPCs

Figure 7 shows flexural strength values for HDPE, W20, AA20, and VA20 composites at 20 wt% wood flour loading. It is clear from the Figure that the acetylation of Scots pine wood flour had a positive effect on the flexural strength. It should be noted that injection-molded WPC even without modification might give slightly higher flexural strength values (Gosselin *et al.* 2006). After acetylation of wood flour, a further increase in flexural strength was observed.

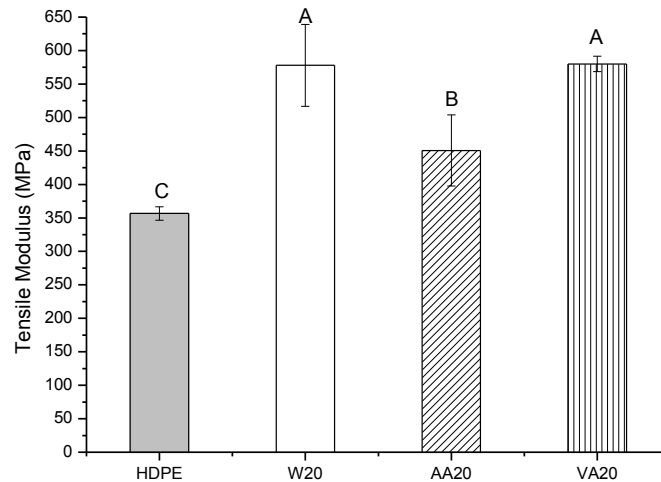


Fig. 6. Effect of acetylation on the tensile modulus values of WPCs

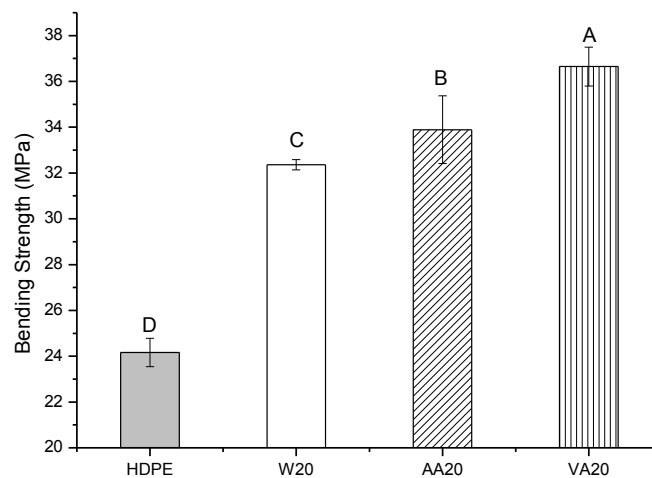


Fig. 7. Effect of acetylation on the flexural strength values of WPCs

The flexural modulus (Fig. 8), similar to the tensile modulus, was increased with the addition of wood flour to the polymer matrix. Acetylation of wood flour with AA slightly reduced these values. A possible reason for reduction of the flexural modulus that AA modified samples (24% WPG) contains 5.8% less lignocellulosic materials than

unmodified wood flour at 20 wt% loading. Because after acetylation treatment, the wood flour gains weight as a result of the presence of bonded acetyl groups in the cell wall, a given weight of modified wood flour therefore contain fewer lignocellulosic materials than unmodified one (Hill 2006).

Figure 9 shows elongation at break values of the HDPE, W20, AA20, and VA20 composites at 20 wt% wood flour loading. It is clear from the Figure that compared to the unfilled HDPE (around 500%), elongation at break values of the composites were significantly lower (around 10%). It is well established that the addition of wood flour to the polymer matrix dramatically reduces the elongation at break values. It is also reported that higher modulus values usually results in lower elongation at break values for this type of composite (Mengelolu and Karakus 2008).

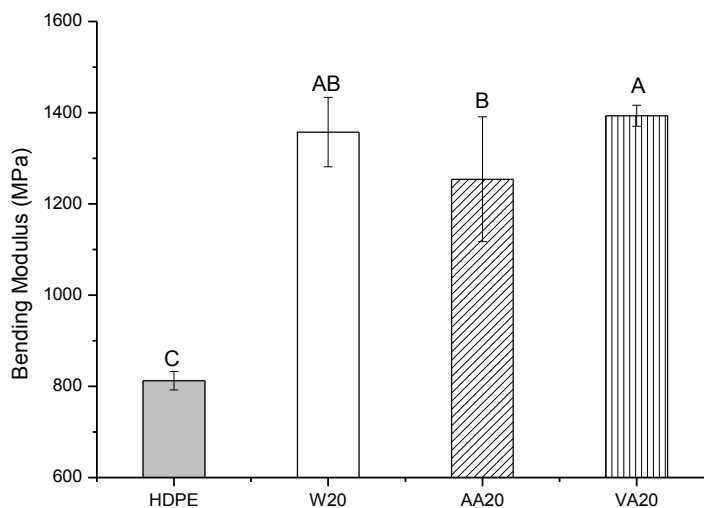


Fig. 8. Effect of acetylation on the flexural modulus values (b) of WPCs

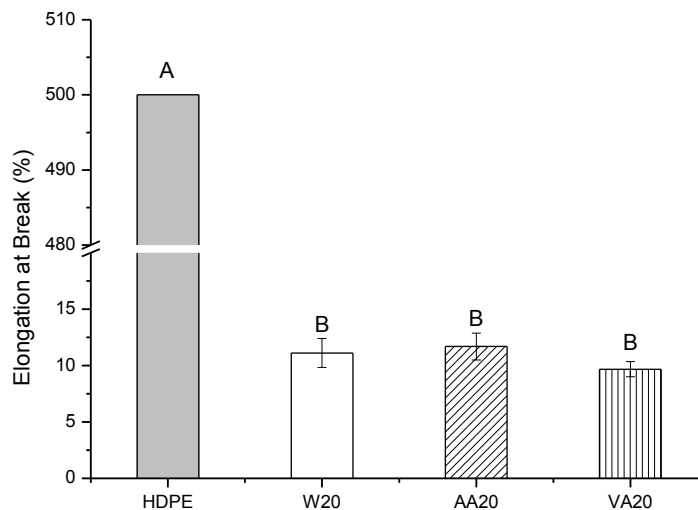


Fig. 9. Effect of acetylation on the elongation at break values of WPCs

Figure 10 presents the impact strength values of the samples. Impact strengths were significantly reduced with the wood flour addition.

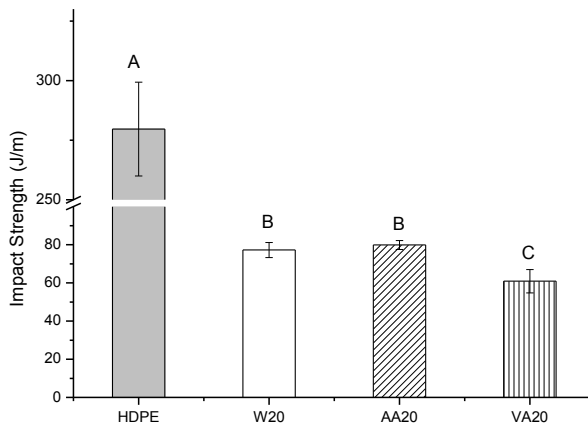


Fig. 10. Effect of acetylation on the impact strength (IS) values of WPCs

Acetylation had no effect on the impact strength. Reduction of the impact strength was reported by Mengeloglu and Karakus (2008) when the commercial coupling agent MAPE was used. This is explained by the fact that better bonding between the polymer and wood flour changed the mode of failure from fiber pullout to fiber breakage. This study was the first time VA was used, and it improved the tensile and flexural strengths as well as the modulus, but not the impact strength. Further studies will be conducted with VA modifications.

The fracture mode of the unmodified wood flour composite (W20) is shown in Fig. 11a. As shown for the freeze-fractured surface, wood fibers are debonded from and pulled out of the cavitated HDPE matrix, which indicates poor interfacial adhesion. The SEM micrographs shown in Figs. 11b and 11c display acetylated wood flour with AA or VA embedded in the HDPE matrix. The acetylated wood flour is coated with a polymer layer and shows good interaction between the two materials.

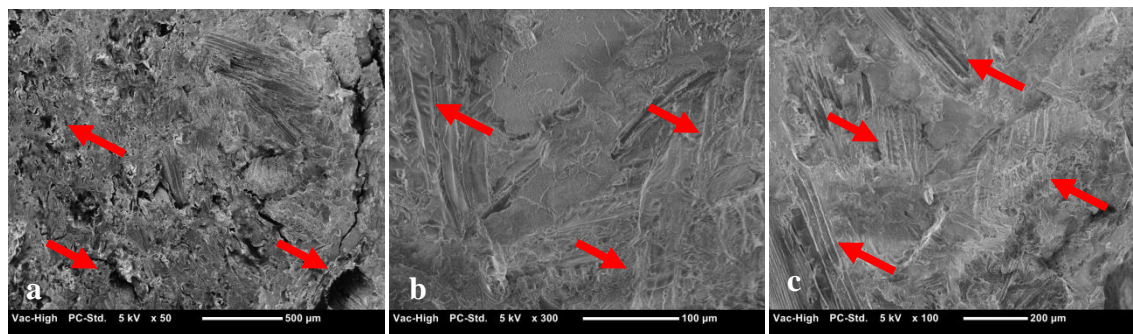


Fig. 11. SEM micrograph of freeze-fractured surface of a) W20 composite (untreated wood flour-reinforced HDPE) illustrating cavitated HDPE matrix, b) AA20 composite (acetic anhydride-modified wood flour-reinforced (24% WPG) HDPE) showing covered wood flour material connecting the wood flour to the matrix, and c) VA20 composite (vinyl acetate-modified wood flour-reinforced (19% WPG) HDPE) showing covered wood flour material connecting the wood flour to the matrix.

The composites reinforced with untreated wood flour and those treated by acetylation (AA or VA) were evaluated by thermogravimetric analysis (TGA) for verification of the thermal characteristics of the materials. This characterization allowed for evaluation of the influence of acetylation treatment of wood flour in the matrix. Figures 12 to 14 show TG curves of W20 (untreated wood flour-reinforced HDPE 20 wt%), AA20 (acetic anhydride-modified wood flour-reinforced HDPE 20 wt%), and VA20 (vinyl acetate-modified wood flour-reinforced HDPE 20wt%) composites.

For the W20 composite (Fig. 12), three stages of thermal decomposition were noticed: 25 to 150°C, 150°C to 400°C, and, 400 to 525°C, which were denoted as region I, region II, and region III, respectively. Complete decomposition of the composite occurred at 525°C. The first stage is related to the release of water or moisture. The second stage is related to the degradation of the wood components of the composite. The third region is related to degradation of HDPE. Similarly, three stages of behavior were also observed with acetylated wood flour-reinforced HDPE composites (Figs. 13 and 14).

For pyrolysis of the untreated wood flour in the HDPE matrix, the active decomposition temperature of the wood flour was determined to be 310°C. For the acetylated wood flour in the HDPE matrix, the main decomposition temperatures of the acetylated wood flour shifted to higher values: 340 and 370°C for AA (Fig. 13) and VA (Fig. 14) modified samples, respectively. It is believed that acetylation with VA enhances the thermal stability properties of lignocellulosic materials.

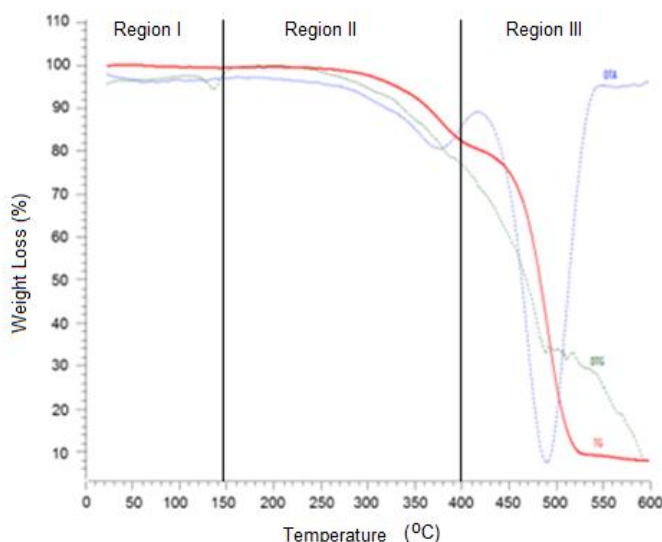


Fig. 12. TGA curves of W20 wood polymer composite

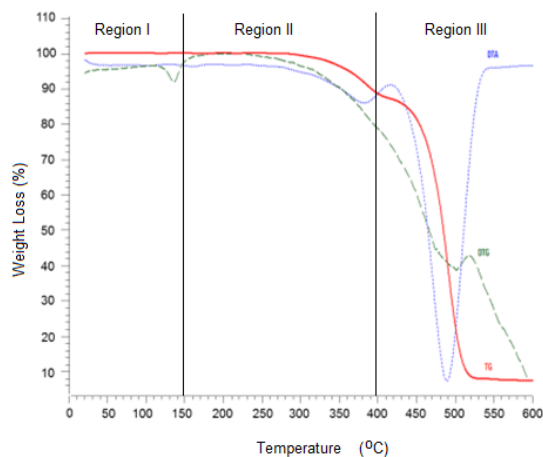


Fig. 13. TGA curves of AA20 wood polymer composite

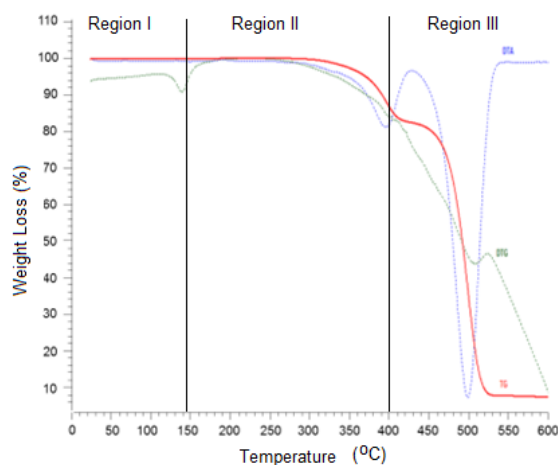


Fig. 14. TGA curves of VA20 wood polymer composite

It was reported in an earlier study that after acetylation of hemp fibers with VA (15% WPG) the active decomposition temperature shifted from 376°C to 392°C (Özmen 2012). The W20, AA20, and VA20 polymer composites consisted of around 6.9%, 5.3%, and 3.4% final ash content, respectively.

CONCLUSIONS

1. Results of AA and VA modification yielded 24% and 19% WPG, respectively. These results were obtained with AA and VA modification under the same reaction conditions.
2. The acetylation of Scots pine flour in a polymer matrix in general results in improvement in tensile strength and tensile and flexural modulus, as well as flexural strength properties compared to neat composite and extracted unmodified wood flour reinforced-composite.
3. The composites reinforced with VA acetylated wood flour exhibited better mechanical properties than the composites with AA acetylated wood flour. It would

be of great interest to investigate the effect of WPG levels of VA modification on the properties of composites in future studies.

4. The addition of wood flour or acetylated wood flour significantly reduces the impact strength compared to neat composites.
5. The composites reinforced with acetylated wood flour presented higher thermal stability than the composites reinforced with untreated wood flour. With acetylation, the maximum weight loss temperature of the wood polymer composites was increased by 30°C (for AA-modified) and 60°C (for VA-modified) when compared with untreated wood flour. Acetylated wood flour with VA exhibited better thermal stability than acetylated wood flour with AA.

ACKNOWLEDGMENTS

This paper has been carried out with financial support from the KSU, BAP 2011-3-YLS29.

REFERENCES CITED

- Abdul Khalil, H. P. S., Issam, A. M., Ahmad Shakri, M. T., Suriani, R., and Awang, A. Y. (2007). "Conventional agro-composites from chemically modified fibers," *Indust. Crops & Prods.* 26(3), 315-323.
- American Society for Testing and Materials (2001). ASTM D638, Standard test method for tensile properties of plastics. ASTM, West Conshohocken.
- American Society for Testing and Materials (2005). ASTM D6109, Standard test methods for flexural properties of unreinforced and reinforced plastic lumber and related products. ASTM, West Conshohocken.
- American Society for Testing and Materials (2005). ASTM D256, Standard test methods for impact resistance of plastics and electrical insulating materials. ASTM, West Conshohocken.
- American Society for Testing and Materials (2007). ASTM D792, Standard test method for density and specific gravity (relative density) of plastics by displacement. ASTM, West Conshohocken.
- Banks, W. B., and Lawther, J. M. (1994). "Cellulosic polymers blends and composites," In *Derivatization of Wood in Composites*, Gilbert, R. D. (ed.), Hanser/Gardner Publications Inc., Cincinnati 131-155.
- Boonstra, M. G., Pizzi, A., Tekely, P., and Pendlebury, J. (1996). "Chemical modification of Norway spruce and Scots pine. A ¹³C NMR CP-MAS study of the reactivity and reactions of polymeric wood components with acetic anhydride," *Holzforschung* 50, 215-220.
- Çetin, N. S. (2000). "Surface activation of lignocellulosics by chemical modification," PhD Thesis, University of Wales Bangor, UK.
- Çetin, N. S., and Özmen, N. (2001). "Dimensional changes in Corsican pine sapwood due to reaction with crotonic anhydride," *Wood Sci. Tech.* 35, 257-267.
- Çetin, N.S., Özmen, N., and Birinci, E. (2011). "Acetylation of wood with various catalysts," *J. Wood Chem. Techn.* 31, 142-153.

- Çetin, N. S., Özmen, N., Tingaut, P., and Sebe, G. (2005). "New transesterification reaction between acetylated wood and tetrametoxysilane: A feasibility study," *Euro. Polym. J.* 41, 2704-2710.
- Felix, J. M., and Gatenholm, P. (1991). "The nature of adhesion in composites of modified cellulose fibers and polypropylene," *J. Appl. Polym. Sci.* 42, 609-620.
- Gosselin, R., Rodrigue, D., and Riedl, B. (2006). "Injection molding of postconsumer wood-plastic composites II: Mechanical properties" *J. Thermoplast. Compos. Mater.* DOI: 10.1177/0892705706067486
- Hill, C. A. S. (2006). "Modifying the properties of wood," In: *Wood Modification: Chemical, Thermal and Other Processes*, John Wiley and Sons, Ltd., England.
- Hon, D. N.-S. (1996). "Functional natural polymers: A new dimensional creativity in lignocellulosic chemistry," In: *Chemical Modification of Lignocellulosic Materials*, Hon, D. N.-S., Marcel Dekker, Inc., New York.
- Jebrane, M., and Sebe, G. (2007). "A novel simple route to wood acetylation by transesterification with vinyl acetate," *Holzforschung* 61(2), 143-147.
- Jebrane, M., Pichavant, F., and Sebe, G. (2011). "A comparative study on the acetylation of wood by reaction with vinyl acetate and acetic anhydride," *Carbohydrate Polymers* 83, 339-345.
- Karnani, R., Mohan, K., and Ramini, N. (1997). "Biofiber-reinforced polypropylene composites," *Polym. Eng. & Sci.* 37(2), 476-483.
- Kokta, B. V., Raj, R.G., and Daneault, C. (1989). "Use of wood flour as filler in polypropylene: Studies on mechanical properties," *Polym. Plast. Tech. Eng.* 28: 247-259.
- Kumar, S. (1994). "Chemical modification of wood," *Wood and Fiber Sci.* 26, 270-280.
- Lisperguer, J., Droguett, C., Ruf, B., and Nunez, M. (2007). "The effect of wood acetylation on thermal behavior of wood-polystyrene composites," *J. Chil. Chem. Soc.* 52(1), 1-6.
- Luz, S. M., Del Tio, J., Rocha, G. J. M., Gonçalves, A. R., and Del'Arco Jr., A. P. (2008). "Cellulose and cellulignin from sugarcane bagasse reinforced polypropylene composites: Effect of acetylation on mechanical and thermal properties," *Composites: Part A* 39, 1362-1369.
- Maldas, D., Kokta, B. V., Raj, R. G., and Daneault, C. (1988). "Improvement of the mechanical properties of sawdust wood fiber-polystyrene composites by chemical treatment," *Polymer* 29, 1255-1265.
- Maldas, D., Kokta, B. V., and Daneault, C. (1989). "Thermoplastic composites of polystyrene: Effect of different wood species on mechanical properties," *J. Appl. Polym. Sci.* 38, 413-439.
- Matsuda, H. (1996). "Chemical modification of solid wood," In: *Chemical Modification of Lignocellulosic Materials*, Hon, D. N.-S. (ed.), Marcel Dekker Inc., New York, 159-183.
- Mat Taib, R., Ramarad, S., and Modh Ishak, Z. A. (2010). "Effect of acetylation and MAPE on the properties of steam-exploded *Acacia mangium* Fiber-HDPE composites," *J. Reinforced Plast. & Comp.* 29(3), 431-444.
- Matuana, L. M., and Balatinecz, J. J. (1998). "Effect of surface properties on the adhesion between PVC and wood veneer laminates," *Polym. Eng. Sci.* 38, 765-773.
- Mengeloglu, F., and Karakus, K. (2008). "Some properties of eucalyptus wood flour filled recycled high density polyethylene polymer-composites," *Turk. J. Agric. For.* 32, 537-546.

- Oksman, K., and Clemons, C. (1998). "Mechanical properties and morphology of impact modified polypropylene wood flour composites," *J. Appl. Polym. Sci.* 67, 1503-1513.
- Oksman, K., and Lindberg, H. (1998). "Influence of thermoplastic elastomers on adhesion in polyethylene wood flour composites," *J. Appl. Polym. Sci.* 68, 1845-1855.
- Özmen, N., Çetin, N. S., Tingaut, P., and Sebe, G. (2007). "Transesterification reaction between acetylated wood and trialkoxysilane coupling agents," *J. Appl. Polym. Sci.* 105, 570-575.
- Özmen, N. (2012). "A study of the effect of acetylation on hemp fibers with vinyl acetate," *BioResources* 7(3), 3800-3809.
- Popa, V. I., and Breaban, I-G. (1995). "Cellulose as a component of biodegradable composites," *Cellulose Chem. & Techn.* 29(5), 575-587.
- Raj, R. G., Kokta, B. V., Maldas, D., and Daneault, C. (1989). "Use of wood fibers in thermoplastics. VII. The effect of coupling agents in polyethylene-wood fiber composites," *J. Appl. Polym. Sci.* 37, 1089-1103.
- Rowell, R. M. (2006a). "Chemical modification of wood: A short review," *Wood Material Sci. & Eng.* 1(1), 29-33.
- Rowell, R. M. (2006b). "Acetylation of wood: Journey from analytical technique to commercial reality," *Forest Prod. J.* 56(9), 4-12.
- Rowell, R. M., Sanadi, A. R., Caulfield, D. F., and Jacobson, R. E. (1997). Utilization of natural fibers in plastic composites: Problems and opportunities. In *Lignocellulosic-plastic Composites*, Leao, A. L., Carvalho, F. X., and Frollini, E. (eds.), Universidade de Sao Paulo Press, Sao Paulo, Brazil, 23-51.
- Sanadi, A. R., Caulfield, D. F., and Jacobson, R. E. (1997). "Agro-fiber thermoplastic composites," In: *Paper and Composites from Agro-Based Resources*, Rowell, R. M., Young, R. A., and Rowell, J. K. (eds.), *CRC Lewis Publishers*, Boca Raton, 378-401.
- Sanadi, A. R., Rowell, R. M., and Young, R. A. (1993). "Evaluation of wood thermoplastic interphase shear strengths," *J. Materials Sci.* 28, 6347-6352.
- Schneider, M. H., and Brebner, K. I. (1985). "Wood-polymer combinations: The chemical modification of wood by alkoxy silane coupling agents," *Wood Sci. Technol.* 19, 67-73.
- Simonsen, J., Jacobson, R., and Rowell, R. M. (1997). "Wood fiber reinforcement of styrene maleic anhydride copolymers," In: *Proceedings of The Fourth International Conference of Woodfibre-Plastic Composites*, Rowell, R. M., and Sanadi, A. R. (eds.), Madison, WI, 215-220.
- Stark, N. M., Matuana, L. M., and Clemons, C. M. (2004). "Effect of processing method on surface and weathering characteristics of wood-flour/HDPE composites," *J. Appl. Polym. Sci.* 93, 1021-1030.
- Tserki, V., Matzinoz, P., and Panayiotou, C. (2006). "Novel biodegradable composites based on treated lignocellulosic waster flour as filler Part II. Development of biodegradable composites using treated and compatibilized waste flour," *Composites: Part A* 37, 1231-1238.

Article submitted: November 5, 2012; Peer review completed: December 8, 2012;
Revised version received and accepted: December 13, 2012; Published: December 14, 2012.