

Cocoa Pod Husks as Potential Sources of Renewable High-Value-Added Products: A Review of Current Valorizations and Future Prospects

Leygnima Yaya Ouattara,^{a,*} Esaie Kouadio Appiah Kouassi,^a Doudjo Soro,^a Yaya Soro,^a Kouassi Benjamin Yao,^a Kopoin Adouby,^a Allali Patrick Drogui,^b Dayal Rajeshwar Tyagi,^b and Pepin Martin Aina^c

Cocoa is among the most cultivated and important tropical crops in the world, and it is economically viable in the agro-pastoral systems of tropical Africa. Further, the amount of cocoa residue is steadily increasing due to the strong worldwide demand for chocolate products. This review of cocoa residue found that an average of 18 publications per year were published in the last 10 years. The most common type of publication on cocoa pod husks (CPH) was newspaper articles, which comprised 50% of the publications. This review examines the use of CHP in sustainable development, agrochemical materials, and agro-materials through their potential valorizations into high value-added products. Indeed, CPH is an abundant, accessible, and renewable resource of bioproducts, dietary fibers, nutraceuticals, functional foods, pectin, antioxidant compounds, theobromine, and minerals. Potential food applications of CPH include the production of flavor compounds, gums, texturing agents, and others. The production of biomaterials for food and non-food use, biofuels, and organic acids, such as lactic acid (the polymerization of which produces the PLA used in bioplastic production), are several potential areas for the biotechnological development of CPH and its fractions.

Keywords: Cocoa pod husks; Pretreatment; Conversion; High value-added products; Biocomposite

Contact information: a: Laboratoire des Procédés Industriels de Synthèse, de l'Environnement et des Energies Nouvelles (LAPISEN), Unité Mixte de Recherche et d'Innovation en Sciences des Procédés Chimiques, Alimentaires Environnementaux et énergétiques, Institut National Polytechnique Félix Houphouët-Boigny, Yamoussoukro, Côte d'Ivoire; b: Institut National de la Recherche Scientifique (INRS Eau Terre et Environnement), Université du Québec, 490 rue de la Couronne, Québec City, Canada; c: Laboratoire des Sciences et Techniques de l'Eau (LSTE)/ Institut National de l'Eau (INE), Université d'Abomey-Calavi (UAC), 01 BP 2009 Cotonou, Benin;

* Corresponding author: leygnima.ouattara18@inphb.ci

INTRODUCTION

Environmental pollution is among the most serious problems facing humanity today (Cho *et al.* 2020). A fundamental problem linked to pollution is the elimination of the large quantities of organic waste that are continuously produced (Cho *et al.* 2020). Solving the problem of large quantities of organic waste or secondary raw materials is a necessity (Balentić *et al.* 2018). Consequently, specific applications are needed to use these raw materials in the most efficient way possible in the production process. The concepts of “wealth-generating waste” and “recyclable materials” are important for building a sustainable and healthy society through the efficient use of these waste resources (Daud *et al.* 2013). As global production of *Theobroma* cocoa beans (Malvaceae) has decreased, the

governments of several tropical countries (Vriesmann *et al.* 2011a) have strongly expressed their support for the expansion of the cocoa industry by encouraging cocoa farmers to plant additional trees. This initiative has led to an increase of more than 50% in the production of cocoa beans (Uy *et al.* 2019). However, the increase in production has also favored the proliferation of undesirable residues, such as cocoa pod husks, on cocoa farms and plantations. In addition, as petroleum resources continue to decrease and the environmental concerns caused by petroleum products grow, research (Vásquez *et al.* 2019) has focused on the capacity of cocoa pod husks to produce biofuels and other biopolymers. However, cocoa pod husk (CPH) remains under-exploited, as it is a renewable resource rich in dietary fiber, lignin, and bioactive antioxidants, such as polyphenols (Lu *et al.* 2018).

The recovery of lignocellulosic fractions and bioactive compounds from cocoa pod husks can lead to the development of profitable basic products. Consequently, these cocoa pod husks can generate income for farmers and promote economic development (Lu *et al.* 2018).

This review article first focuses on analyzing bibliometric data to determine the trends, research priorities, current topics, and important research areas of cocoa pod husks. Then, the stages in the development of CPH are presented to summarize the mineral and biochemical composition of CPH. The main pretreatment strategies and the different ways of converting cocoa pod husks are also reviewed. Finally, the current state of CPH valorization and future perspectives on CPH valorization are discussed.

Dynamics of the Production of Beans and Cocoa Pod Husks

Approximately 50 countries produce cocoa, and the Ivory Coast is the largest producer. Figure 1 (International Cocoa Organization (ICCO)) shows the evolution of cocoa production in west Africa. The African continent alone supplies approximately 74% of cocoa produced globally. Among various countries of Africa, Ivory Coast is the biggest producer of cocoa (42%), followed by Ghana (20%), Nigeria (6%), and Cameroon (5%). Figure 1 provides the statistics of cocoa production in cocoa-producing countries. However, Ivory Coast suffers many consequences due to its immense production.

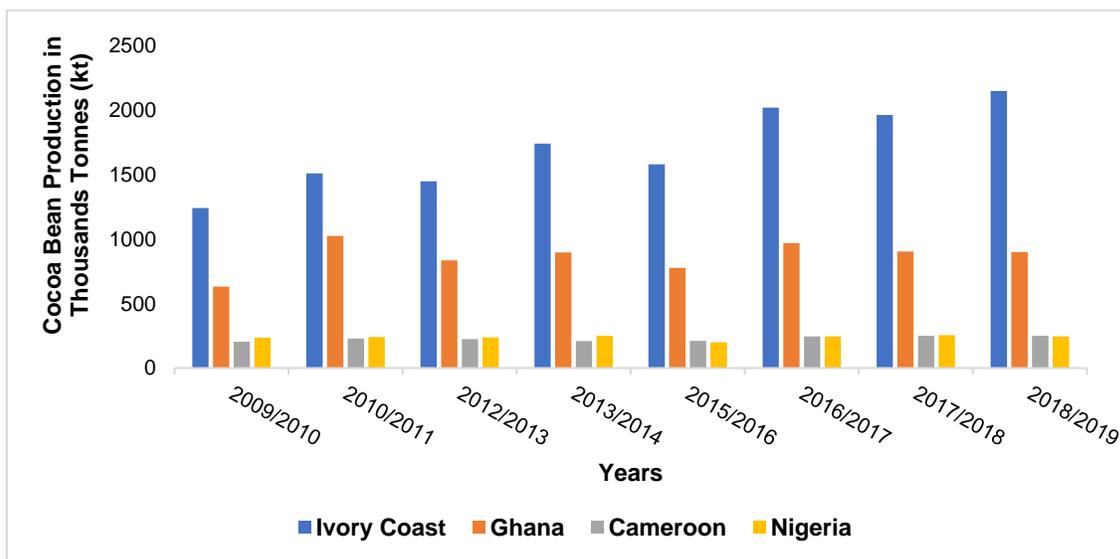


Fig. 1. Quantity of cocoa beans per y in the main producing countries of West Africa (International Cocoa Organization (ICCO) 2019)

In fact, 10 tonnes of wet pods are generated for each tonne of dry cocoa beans (Campos-Vega *et al.* 2018). Therefore, a large area is necessary for disposal, and the wet pods represent a major challenge for waste management. Currently, in Ghana and Ivory Coast, approximately 1% of this biomass is used to make soap (Antwi *et al.* 2019).

Figure 2 shows the amounts of beans and cocoa pods husks produced in the main cocoa-bean producing countries during the 2018/2019 campaign. As Ivory Coast produced approximately 6,500,000 tonnes of CPH, it now must manage this waste, which is generally stored in fields, and its decomposition attracts flies and other insects harmful to cocoa. Furthermore, the decomposition of these residues is a potential source of pathogenic microorganisms, such as black pod disease (Mansur *et al.* 2014), which is caused by *Phytophthora palmivora* and *P. megakarya* fungi. The disease causes an estimated annual yield loss of 20% to 30% worldwide, whereas individual farms may experience an annual yield loss of 30% to 90% (Lu *et al.* 2018).

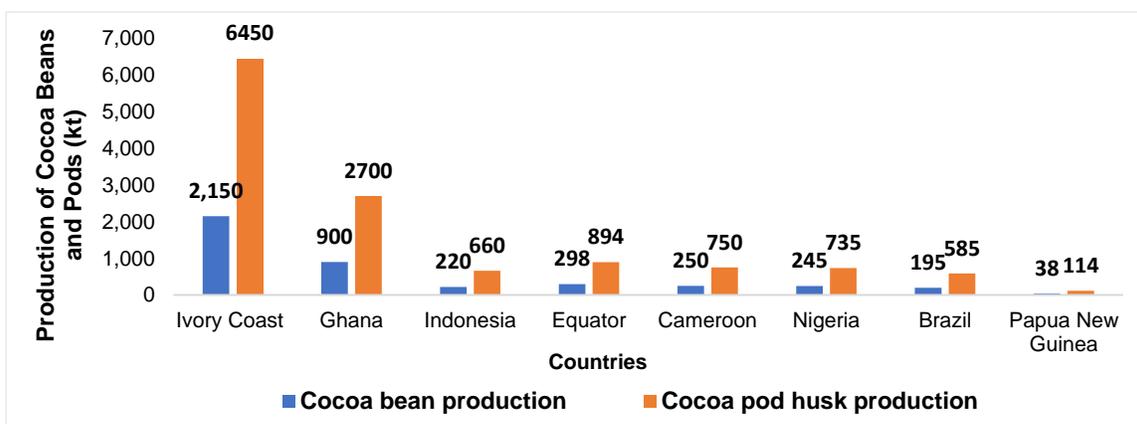


Fig. 2. Production of cocoa beans and residual pod by country during 2018 and 2019 (Statista 2019)

Cocoa pod husk is a lignocellulosic biomass that is rich in minerals (in particular, potassium), fibers (especially lignin, cellulose, hemicellulose, and pectin), and antioxidants (phenolic acids, *etc.*) (Kouakou *et al.* 2018). However, it is still largely under-exploited. Appropriate use of this lignocellulosic material could offer economic benefits and reduce its environmental impact (Adjin-Tetteh *et al.* 2018).

Description of CPH

The CPH is the outer part of the fruit (exocarp), which has an oval, rough, and relatively thick appearance (Fig. 3 and Fig. 4).

Cocoa pod husk comes in different colors depending on the variety, and its roughness protects it against the elements, plagues, and damage that could be caused by impact (Vásquez *et al.* 2019). It is obtained after husking and removing the beans, and it represents 70% to 80% of the dry weight of the whole fruit. This natural, layered material comprises three distinct layers (Fig. 4), which are the epicarp, the mesocarp, and the endocarp, which constitute the outer, middle, and inner pericarp, respectively (Campos-Vega *et al.* 2018). The endocarp is the innermost part and occurs as a soft, whitish tissue that protects the cocoa beans in a well-lubricated inner chamber (Campos-Vega *et al.* 2018). The mesocarp has a hard composite structure capable of holding the cocoa beans in place even in severe conditions.



Fig. 3. Cocoa pod husks

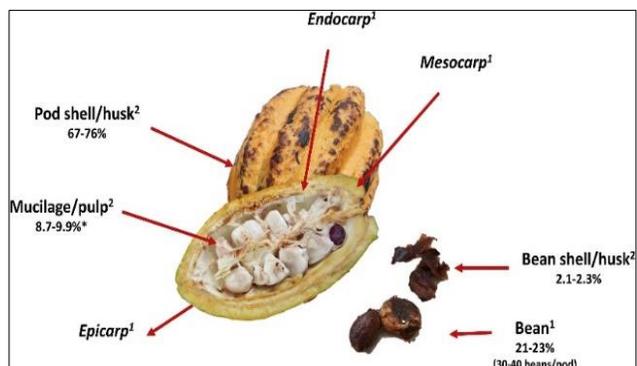


Fig. 4. Different parts of CPH (Reprinted with permission; Campos-Vega *et al.* 2018)

The relatively soft outermost layer is the yellow (or purplish red upon maturity) cover, and it is this part that is exposed to the sun. When it turns black, this indicates that the fruit is rotting and dry (Babatope 2005).

Bibliometric Study on the Cocoa Pod Husk

Bibliometric analysis is a useful tool for analyzing publications in several areas of research (Maassen 2016). It is a quantitative approach of studying the metadata of scientific publications (Maassen 2016). It is a useful method for detecting research trends in a given area (Maassen 2016). It concerns three elements of scientific activity, which are its inputs, its outputs, and its impacts. It allows an assessment of scientific activity and the place of actors in relation to a given theme. This new scientific approach has been increasingly used and considered before undertaking studies on a given theme.

In this study, several word combinations were searched to identify themes from 2005 to 2019, which included “cocoa pods,” “cocoa pod husks,” and “cocoa residues.” With this method, it was possible to overcome the weaknesses of individual keyword analysis and identify relevant points and current search trends in different countries (Maassen 2016) for a given theme. This bibliometry on CHP was produced on 05/07/2019 with the internet platform SCIFINDER that lists all forms of publication dealing with the topic to be addressed. This database allowed assessment of the scientific interest in the subject of CPH. A total of 268 publications met the selection criteria. The selected publications were then analyzed according to the characteristics of the articles (type of document, country of origin, and citations), publication models (main journals and journal category), the importance of research (number of publications per year), the number of publications per author, and the areas of valuation (Maassen 2016).

Number of Publications per Year

Interest in CPH began in 1905 with a single publication. However, an increased interest in CPH began in 2003 and has continued to grow (Fig. 5). Over the past 10 y, an average of 18 publications per year have been produced on CPH. Over the past 5 y, an average of 24.2 publications per year were produced. This growing interest in cocoa pod husks is probably due to the increasing amount of this residue in the fields, which is becoming an environmental problem. Further, the enormous losses caused to cocoa farmers due to cocoa diseases, such as brown and black pod rot, have likely driven this interest.

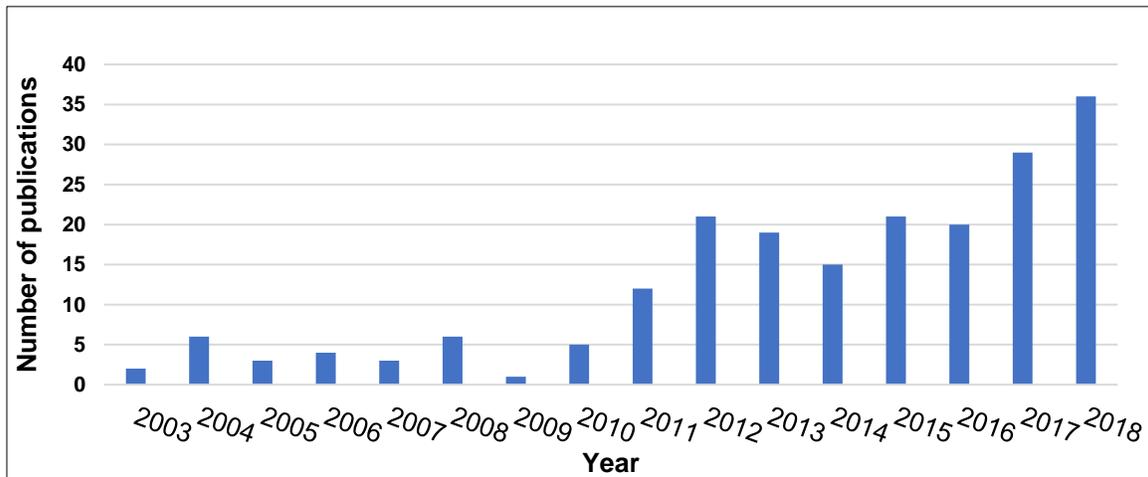


Fig. 5. Number of publications produced annually related to CPH

In addition, the demand for chocolate-based products has led cocoa-producing countries to increase their production, which has resulted in increased waste products, such as CPH, which constitutes approximately 76% of the weight of whole pods (Chun and Husseinsyah 2016). Several studies have shown that 10 tonnes of CPH are produced as waste for every tonne of cocoa beans (Mansur *et al.* 2014; Sanyang *et al.* 2017). Therefore, the theme related to this material was topical and relevant to the interest of researchers.

Work Density by Publishing Type

The most common type of publication on CPH was journal articles, which comprised 54% of the publications (Fig. 6). Therefore, CPH has great potential and requires further exploration based on the number of patents filed (12), which represented 15% of publications. A single bibliographic review article was produced on CPH, which looked at the biotechnological recovery of all residual biomass from the cocoa industry (Vásquez *et al.* 2019) and justified the present study. Figure 6 illustrates the distribution of publication types.

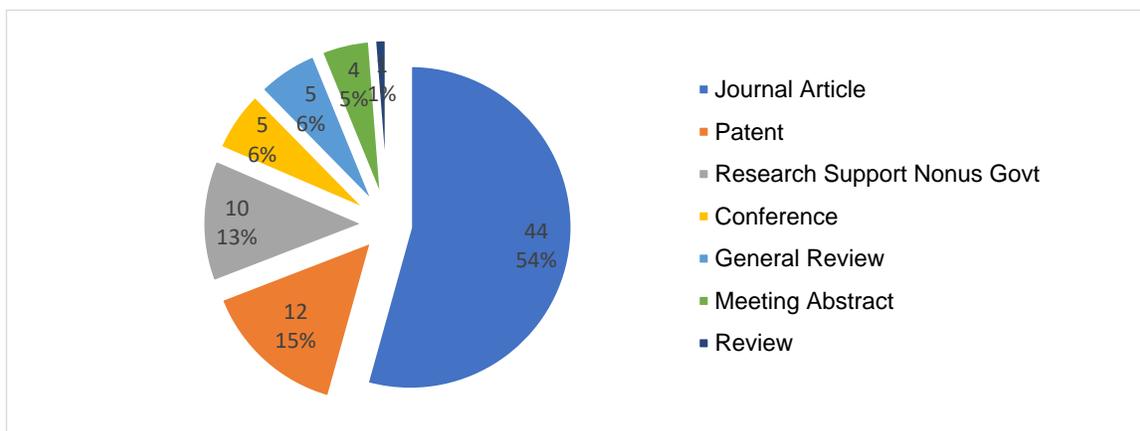


Fig. 6. Density of works by type of publication

Areas of Valorization for Cocoa Pod Husks

The valorization of CPH has aroused interest in several fields, including radial electrochemical agrochemical bioregulators, thermal energy technology, soil fertilization, plant nutrition, food and animal chemistry, plastic treatment, and waste treatment and disposal (Fig. 7).

The large numbers of publications in the fields of soil fertilization, plant nutrition, food and feed chemistry, plastics manufacturing and processing, and waste treatment and disposal were justified by the rich mineral and fibre composition of this biomass. Several of these areas (soil fertilization, plant nutrition, and food and feed chemistry) have already been widely exploited and others (plastic manufacturing and processing) are still under study and deserve special attention.

The recovery of CPH begins with the harvest of the material, followed by drying. Indeed, the moisture content of the fresh pod is approximately 90% (Vriesmann *et al.* 2011a).

Therefore, quick drying is essential to avoid deterioration. Finally, the CPH residues are ground. A complete characterization (physico-chemical, biochemical, and thermal) and an appropriate delignification process are necessary to better explore the lignocellulosic components of CPH to identify the appropriate pathway for the residue.

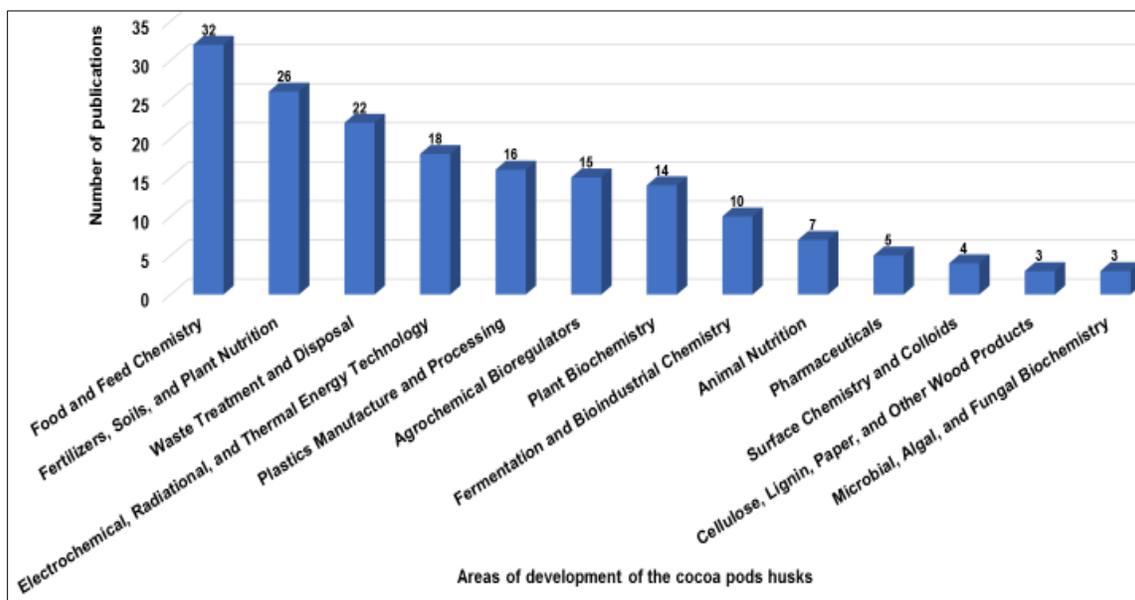


Fig. 7. Publications of the Index of Scientific quotes based on the areas of CPH valuation

Cocoa Pod Husks Valorization Process

Chemical, Physico-chemical, and Biochemical Characterization Process of Cocoa Pod Husks

Figure 8 schematically illustrates the valorization process of CPH in value-added products. Several works have focused on the physico-chemical (Vásquez *et al.* 2019), thermochemical (Adjin-Tetteh *et al.* 2018), and biochemical (Giwa *et al.* 2020), characterization of CPH to identify the appropriate conversion pathways. Cocoa pod husks were found to be rich in raw energy, cellulose, hemicellulose, potassium, and many other minerals useful for soil improvement.

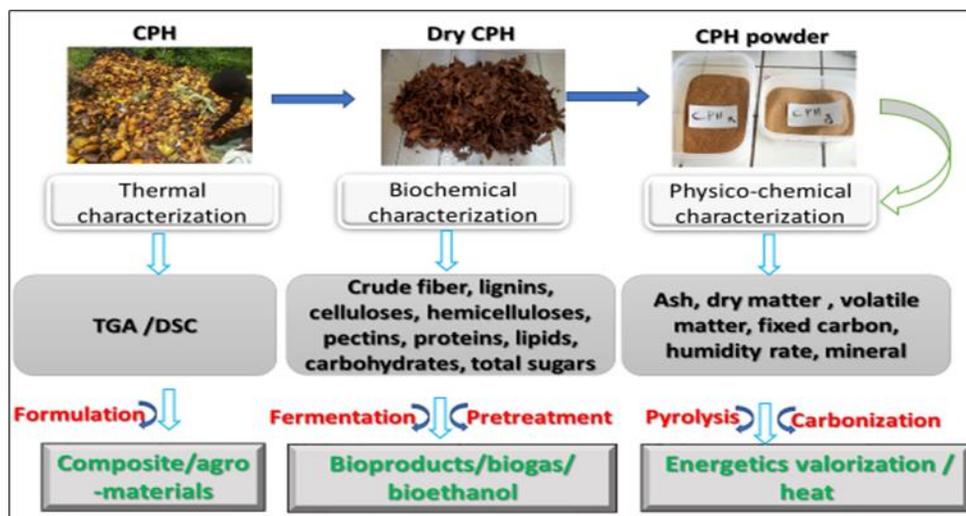


Fig. 8. Schematic representation of the characterization procedures of cocoa pod husks

Table 1 summarizes the proximal composition of CPH obtained in several regions of the world after its characterization.

Table 1. Composition of Cocoa Pod Husks in Previous Studies

Volatile Matter (%)	Ash (%)	Moisture (%)	C _{fixe} (%)	Reference
58.46	13.21	11.53	16.80	Forero Nuñez <i>et al.</i> (2015)
61.73	16.24	11.07	10.96	Adjin-Tetteh <i>et al.</i> (2018)
68.47	10.81	10.29	10.43	Titiloye <i>et al.</i> (2013)
70.40	10.90	14.00	16.70	Kilama <i>et al.</i> (2019)
49.90	13.50	16.10	20.50	Syamsiro <i>et al.</i> (2012)
64.19	15.31	10.10	10.40	Asiedu <i>et al.</i> (2019)
58.75	06.99	14.43	19.83	Chan and Choo (2013)
92.60	07.39	-	-	Antwi <i>et al.</i> (2019)
-	07.40	11.04	-	Nazir <i>et al.</i> (2016)

Note: “-” = Not defined

Knowing of the moisture content of a biomass is crucial for the choice of the energy conversion method available for processing this biomass. According to Tsai *et al.* (2017), moisture content has a direct impact on the calorific value of a biofuel. The values obtained during various studies were all over 10%. Thus, the residue would be better suited for biochemical conversion than thermal conversion (Adjin-Tetteh *et al.* 2018). Further, moisture in the raw material can act as a binder (Adjin-Tetteh *et al.* 2018) and lubricant by improving the gelatinization of starch and facilitating the formation of van der Waals forces (Adjin-Tetteh *et al.* 2018) and the possible diffusion of water-soluble substances in the matrix of the raw material (Titiloye *et al.* 2013). The ash contents of the different samples were quite high, which reflected a higher level of inorganic substances that can act as catalysts for the whole thermal conversion process (Titiloye *et al.* 2013). Tables 2 and 3 present the lignocellulosic and mineralogical composition of CPH in different studies around the world.

Table 2. Biochemical Composition of CPH in Previous Studies

Lignin (%)	Cellulose (%)	Hemicellulose (%)	Pectin (%)	Reference
24.16	28.25	16.75	-	Sandesh <i>et al.</i> (2020)
12.06	18.42	10.04	-	Marsiglia <i>et al.</i> (2016)
14.70	35.40	37.00	-	Daud <i>et al.</i> (2014)
33.96	30.41	11.97	-	Titiloye <i>et al.</i> (2013)
14.00 to 28.00	19.70 to 26.10	8.70 to 12.80	06.00 to 12.60	Lu <i>et al.</i> (2018)
18.19	23.04	38.08	-	Asiedu <i>et al.</i> (2019)
14.60 to 26.38	24.24 to 35.00	8.72 to 11.00	6.10 to 9.20	Vásquez <i>et al.</i> (2019)
34.82	44.69	11.15	10.10 ± 0.3	Nazir <i>et al.</i> (2016)

Note: "-" = Not defined

An analysis of Table 1, Table 2, and Table 3 illustrates the rich lignocellulosic and chemical composition of CPH, which could lead to its use as a potential substrate for anaerobic digestion (Rastegari *et al.* 2019) to produce bioactive compounds.

Table 3. Chemical Composition of CPH in Previous Studies

Phosphorus (P)	Potassium (K)	Calcium (Ca)	Magnesium (Mg)	Iron (Fe)	Manganese (Mn)	Sodium (Na)	Zinc (Zn)	Reference
-	2.768	0.254	0.111	0.0058	0.036	0.0105	0.0397	Vásquez <i>et al.</i> (2019)
-	3.77	0.46	0.25	0.003	-	0.016	-	Gyedu-Akoto <i>et al.</i> (2015)
0.19	2.8 to 3.8	0.25 to 0.46	0.11 to 0.25	0.003 to 0.06	-	0.01 to 0.02	-	Lu <i>et al.</i> (2018)
0.39	3.22	0.30	0.00	0.035124	0.005010	0.45	0.005623	Antwi <i>et al.</i> (2019)
0.10	3.40	0.60	0.40	-	-	0.00	-	Djeke <i>et al.</i> (2011)

Note: Units are (g / 100 g of dry matter)

These bioactive compounds have many applications, which include renewable energy, biopolymers, formulating plasticized composites, and acting as a fertilizer element (Djeke *et al.* 2011; Kouakou *et al.* 2018).

The disparities observed between the physico-chemical and biochemical compositions of the CPH could have been due to geographic factors, the location of the materials collected, the different methods of analysis, the variety of biomass, the differences in the solvents used, the different collection periods (Sandesh *et al.* 2020), and the different climatic and storage conditions (Titiloye *et al.* 2013), among other factors.

Lignocellulosic Biomass Pretreatment

Lignocellulosic biomass is a renewable material that can be converted into fermentable sugars and then converted into ethanol (Rezania *et al.* 2017). However, this convention is hampered by the recalcitrant nature of this plant biomass (Woiciechowski *et al.* 2020) due to the presence of lignin and the consequent difficulty of obtaining complete

enzymatic hydrolysis has led to the implementation of different pretreatment strategies (Beukes and Pletschke 2010). Pretreatment aims to modify the properties of raw materials, to remove or dissolve lignin and hemicellulose, and to reduce the crystallinity of cellulose (Thamsee *et al.* 2019). It is performed to increase the surface accessible to hydrolytic enzymes (Wang *et al.* 2015). The pretreatment process further alters the microstructure, macrostructure, and chemical composition of lignocellulose to improve the efficiency of the hydrolysis of sugars (Chandra *et al.* 2015) to make them accessible to microbial degradation (An *et al.* 2015). The pretreatment process improves the efficiency of and stimulates sugar hydrolysis (Chandra *et al.* 2015). As the separation of carbohydrates from lignocellulose is a key step in the process, the choice of pretreatment strategy is crucial to facilitate the transformation of lignocellulosic biomass into products with high added value (Arevalo-Gallegos *et al.* 2017). The four pretreatment strategies are physical, chemical, physico-chemical, and biological.

In general, chemical and physicochemical pretreatments give good results. However, excessive use of chemicals could lead to serious environmental problems (Chen *et al.* 2017). The biological method consumes less energy and is less polluting than other methods, but it is expensive and time consuming, and enzyme activity in the decomposition of lignocellulose is low (Chen *et al.* 2017).

The following section discusses the pretreatment technologies commonly used in the recovery of lignocellulosic biomass in general and those applied to valorize CPH in particular.

Pretreatment with acid solution

Acid pretreatment is a highly effective chemical technique used to break down the lignocellulosic matrix by cleavage of the glucosidic bonds (Woiciechowski *et al.* 2020). Acid pretreatment mainly solubilizes hemicelluloses and part of the lignin (Woiciechowski *et al.* 2020). Inorganic acids ((sulfuric acid (H₂SO₄), nitric acid (HNO₃), and phosphoric acid (H₃PO₄)) and organic ones (formic acetic and propionic acid) (Aslanzadeh *et al.* 2014) are generally used. However, most concentrated acids are highly toxic and corrosive, so the acid must be recovered, and the equipment used must be resistant to acid corrosion (Manzoor *et al.* 2013; Laurens *et al.* 2015; Chen *et al.* 2017). This results in high operational and maintenance costs, and the process destroys hemicellulosic sugars and transforms them into toxic compounds, such as acetic acid, furfural, and 5-hydroxymethylfurfural (5-HMF), which inhibits microbial growth (Woiciechowski *et al.* 2020). However, the conversion rate to sugar is higher than pretreatments that use hydrochloric acid, phosphoric acid, or nitric acid (Mosier *et al.* 2005; Sandesh *et al.* 2020). The optimization of biogas production by applying acid (H₂SO₄) pretreatments to CPH has been achieved (Ward-Doria *et al.* 2016). Likewise, cocoa pod husks have been used to release reducing sugars using autoclave-assisted hydrochloric acid hydrolysis to obtain reducing sugars (Shet *et al.* 2019). The concentration of hydrochloric acid (HCl) and the duration of the autoclave were used to optimize the hydrolysis process. Under optimized conditions 21.11 g/L of reducing sugar were released (Shet *et al.* 2019). Otherwise, a study by Dahunsi *et al.* (2019a) showed that cocoa pods husks could produce up to 71% biogas *via* the mono-fermentation of CPH pretreated with sulfuric acid (H₂SO₄) and alkaline hydrogen peroxide (H₂O₂). Additionally, xylitol has been produced from xylose from cocoa pod husks using sulfuric acid pretreatment, optimized by the response surface methodology (Santana *et al.* 2018). Xylitol was obtained at concentrations of 11.34 g.L⁻¹, corresponding to a yield (Y p/s) of 0.52 g.g⁻¹ with a fermentation efficiency of 56.6 %.

Alkaline pretreatment

Alkaline pretreatment is an economical process that is carried out by soaking a ground biomass in a basic solution at relatively low temperatures and pressures (Beukes and Pletschke 2010; Umagiliyage *et al.* 2015). It is an interesting technology, in which the formation of few fermentation inhibitors occurs (Beukes and Pletschke 2010). This pretreatment increases the surface area exposed to enzymatic hydrolysis and the accessibility of cellulose by removing the acetyl and uronic acid substituents associated with hemicelluloses (Umagiliyage *et al.* 2015). The alkaline solutions of sodium hydroxide (NaOH), potassium hydroxide (KOH), calcium hydroxide (Ca(OH)₂), and ammonium hydroxide (NH₄OH) are suitable for the pretreatment of lignocellulose (Mirmohamadsadeghi *et al.* 2016; Saratale *et al.* 2016). For example, Ca (OH)₂ can remove the acetyl group from hemicellulose to increase the digestibility of cellulose and reduce the steric hindrance of enzymes (Chen *et al.* 2017). Then, Ca(OH)₂ can increase the crystallinity index by eliminating amorphous substances (Chen *et al.* 2017). The optimal pretreatment conditions (Ca(OH)₂ and NaOH) for sweet sorghum bagasse have been determined (Umagiliyage *et al.* 2015). Expected yields of 85.6% biomass to biofuel conversion and 35.5% lignin removal can be achieved.

Several upgrading processes that employ CPH as recoverable biomass have integrated alkaline pretreatment and led to the production of biogas from the anaerobic co-digestion of CPH and poultry manure after pretreatment with sulfuric acid and hydrogen peroxide (Dahunsi *et al.* 2019b). The use of alkaline hydrogen peroxide resulted in solubilization of up to 81% of the lignin from the CPH.

The optimization of biogas production by applying acid (H₂SO₄) and alkaline (NaOH) pretreatments to CPH has been achieved (Ward-Doria *et al.* 2016), and the alkaline pretreatment gave the best result of up to 43.8% delignification. The effect of reagent type (sodium hydroxide (NaOH), alkaline peroxide (H₂O₂), and sulfuric acid (H₂SO₄)) was also evaluated on the delignification of CPH using response surface methodology (Nazir *et al.* 2016). The alkaline pretreatment still had the best results independent of reagent type.

Steam-explosion pretreatment

The steam-explosion process is among the most widely used physico-chemical pretreatment processes. This process occurs when water vapor is subjected to a high temperature for a few seconds to several minutes and then rapidly expelled from the reactor (Chen *et al.* 2017). The flow of vapor and liquid material cools rapidly due to the reduced pressure (Chen and Liu 2015). The main mechanism of the process is the high-pressure vapor in the fibers that causes the mechanical breakdown of the fiber. It is an inexpensive option for the pretreatment of agricultural residues, and it has a considerably reduced environmental impact (López-Linares *et al.* 2015). It has a lower environmental impact, lower requirements in terms of reaction conditions and cost, and fewer risks linked to chemical reagents and complete recovery of sugar than other methods. Further, this pretreatment leads to the formation of degradation products of sugars, such as acetic acid formed by the self-hydrolysis of acetyl groups at elevated temperatures or many phenolic compounds (Chen *et al.* 2017). This could justify why no valuation study of CPH has mentioned the application of steam-explosion pretreatment.

Explosion of ammonia-pretreated fibers

The explosion-of-ammonia-fiber (AFEX) pretreatment is a combination of steam-explosion pretreatment and alkaline pretreatment in anhydrous ammonia at high

temperature (90 °C to 100 °C) and high pressure (1 MPa to 5.2 MPa) (Chen *et al.* 2017). After a rapid release of pressure, the ammonia is vaporized, which leads to a sudden change in temperature. As a result, the structure of the biomass is severely damaged, thus exposing the cellulose surface to increased enzymatic hydrolysis (Chen *et al.* 2017). The main advantage of AFEX pretreatment is the absence of substances that inhibit microbial fermentation. This process also produces a residue of ammonium salt that can serve as a nutrient for microbial fermentation (Chen *et al.* 2017). Thus, the resulting hydrolyzate after pretreatment can be directly used without further specific treatment. Under these conditions, AFEX is therefore suitable for the pretreatment of agricultural waste and herbaceous plants that contain a high content of cellulose (Wyman *et al.* 2005). However, the ammonia used must be recycled due to its high cost and volatility (Taherzadeh and Karimi 2008). However, to our knowledge, no study in the literature has yet explored the use of pre-blast pretreatment of cocoa pods husks fibers with ammonia.

CO₂-explosion pretreatment

The CO₂-explosion pretreatment combines steam explosion and the addition of CO₂ to form carbonic acid, the presence of which greatly improves the efficiency of hemicellulosic hydrolysis (Chen *et al.* 2017). This process has enormous advantages, including the absence of inhibitors during subsequent fermentation; further, it is non-toxic, non-flammable, and cost-effective (Chen *et al.* 2017). In addition, the surface of the resulting substrate is easily accessible to subsequent enzymatic attack. A Box-Behnken design was applied to supercritical CO₂ extraction to develop an appropriate ecological process to obtain a soluble fraction rich in phenolic compounds from CPH (Alemawor *et al.* 2009).

Microwave pretreatment

Microwave technology makes cellulose more responsive and improves the accessibility and adaptability of the lignocellulosic feedstock to enzymes (Chen *et al.* 2017). It is an energy efficient technology that is applicable in chemical reactions (Chen *et al.* 2017). Several studies have focused on microwave pretreatment of fibrous raw materials (Manzoor *et al.* 2013; Lo *et al.* 2015). Microwave pretreatment allows a subsequent increase in enzyme activity (Chen *et al.* 2017), but it requires a high investment. Microwave-assisted pretreatment optimization of CPH using sulfuric acid (H₂SO₄) was also performed by comparing the efficiency of the response surface methodology to that of the network of artificial neurons to produce bioethanol (Shet *et al.* 2018b), and a maximum of 9.10 g/L of sugars was released.

Biological method

The degradation of lignin is facilitated by biological pretreatment, as it can generate enzymes that break down lignin during the process. Biological pretreatment usually uses wood-rotting fungi (Chen *et al.* 2017). Different lignocellulosic biomasses have been biologically pretreated using fungi, such as white rot, *Ceriporiopsis subvermispora*, *Pleurotus ostreatus*, *Ceriporia lacerata*, *Cyathus stercoleris*, *Pycnoporus cinnabarinus*, and *Phanerochaete chrysosporium*, on different lignocellulosic biomasses (Chen *et al.* 2017). Thus, the biological pretreatment of CPH has been carried out *via* the use of fungal species *chrysosporium* of the genus *Phanerochaete* (Laconi and Jayanegara 2015), and this species has shown its effectiveness in improving the nutritional value of CPH. Similarly, *Pleurotus ostreatus* (Alemawor *et al.* 2009) reduced cellulose, hemicellulose, and lignin

content by 6 wt%, 3 wt%, and 6 wt%, respectively, with manganese ion supplementation (Mn^{+2}). These results show that the *Pleurotus* species has promising cellulolytic and hemicellulolytic activity on CPH (Alemawor *et al.* 2009). Table 4 summarizes past work on the pretreatment of CPH.

Table 4. Main Pretreatment Strategies Applied to Cocoa Pod Husk in Previous Studies

Pretreatment Method	Intended Use	Yield	Reference
Chemical (Na_2CO_3)	Optimization (reducing sugars)	0.94 g/L	Shet <i>et al.</i> (2016)
Chemical (H_2SO_4 , NaOH)	Optimization (delignification)	74.48%	Nazir <i>et al.</i> (2016)
Chemical (H_2SO_4 , NaOH)	Biomethane production	0.247 m ³ CH ₄ /kg VS	Ward-Doria <i>et al.</i> (2016)
Chemical (NaOH), sonification	Microcrystalline cellulose	286 nm	Jimat <i>et al.</i> (2016)
Chemical (H_2SO_4)	Bioethanol production	2 g/L	Shet <i>et al.</i> (2018a)
Chemical (H_2SO_4 , H_2O_2)	Biogas production	243.3 ± 4.1 l(N)/kg VS	Dahunsi <i>et al.</i> (2019a)
Mechanical (grinding)	Methane production	22%	Dahunsi (2019)
Hydrothermal	Biogas production	526.38 l(N)/kg VS	Antwi <i>et al.</i> (2019)
Biological (<i>Phanerochaete chrysosporium</i>)	Feed production for ruminants	Increased digestibility (28.5%)	Laconi and Jayanegara (2015)
Biological (<i>Pleurotus ostreatus</i>)	Improving nutritional status	17% Reduction (crude fiber and lignin)	Alemawor <i>et al.</i> (2009)
CO ₂ explosion	Phenolic compounds	12.97 mg GAE/g	Valadez-Carmona <i>et al.</i> (2018)

Note: GAE = Gallic acid equivalent; Cumulative gas potential = (l(N)/kg VS)

Cocoa Pod Husk Conversion Processes

Several conversion routes (physical, biochemical, and thermochemical) of biomass into products with high added value, such as biofuels and biochemicals, have been exploited (Tsai *et al.* 2017; Adjin-Tetteh *et al.* 2018). Volatile materials are suitable for combustion, gasification, and pyrolysis. As the volatility of a given material increases, the ignition speed of the resulting biofuel increases (Chan and Choo 2013). However, among thermochemical conversion technologies, pyrolysis has sizable advantages over other biomass and waste processing technologies (Adjin-Tetteh *et al.* 2018). Pyrolysis is the decomposition of matter under the influence of water vapor (Chen *et al.* 2017). During the pyrolysis process, cellulose decomposes rapidly when heated to above 300 °C, which results in the release of gaseous products and the production of coke-like residues (Chen *et al.* 2017). In addition, other polysaccharide degradation products, such as furfural and aldehydes, can form in the presence of acid and limit microbial fermentation (Laser *et al.* 2002). This treatment is applied only when the biomass has a solids content less than 20%, which results in high energy consumption and relatively low productivity (Laser *et al.* 2002). The high-value-added bio-oil it produces can compete with and potentially replace non-renewable fossil fuels (Adjin-Tetteh *et al.* 2018).

Cocoa pod husk has been shown to be an excellent raw material for pyrolysis reactions (Adjin-Tetteh *et al.* 2018). Moreover, CPH contains a mixture of cellulose,

hemicellulose, lignin, pectin, and crude fibers in large proportions. Therefore, it is a potential source of biomass substrates for biochemical production (Adjin-Tetteh *et al.* 2018). Indeed, a study on the technical-economic evaluation of five lignocellulosic biomass-treatment technologies (Maleka 2016) concluded that the two most effective treatment technologies for the recovery of cocoa pod husks are hydrothermal carbonization and anaerobic fermentation (Maleka 2016). Others studies have used CPH as a renewable energy source and analyzed its characteristics in a combustion chamber (Syamsiro *et al.* 2012). The crushed bales were charred at 400 °C for 2 h, which resulted in a higher calorific rate ($17 \text{ M} \times \text{Kg}^{-1}$) with a high ash content.

Table 5. Main Conversion Processes Applied to Cocoa Pod Husk

Conversion Pathways		Applications	Reference
Thermochemical	Hydrothermal carbonization	- Phenolic compounds and sugars - Bio-oil production - Briquette production	Hernández-Hernández <i>et al.</i> (2019) Ogunjobi and Lajide (2015) Ofori and Akoto (2020)
	Direct Combustion	- Heat energy production	Syamsiro <i>et al.</i> (2012)
	Gasification	- Energy production	Martínez-Ángel <i>et al.</i> (2015)
	Pyrolysis	- Biochar production	Tsai <i>et al.</i> (2017)
		- Amoxicillin and ibuprofen elimination	Tovar <i>et al.</i> (2018)
		- Bio-oil	Adjin-Tetteh <i>et al.</i> (2018)
		- Biofuel	Akinola <i>et al.</i> (2018)
- Pyrolysis oil	Mansur <i>et al.</i> (2014)		
Biochemical	Anaerobic Digestion	- Bio-oil and biogas	Chan and Choo (2013)
		- Energy production	Acosta <i>et al.</i> (2018)
		- Biogas production	Antwi <i>et al.</i> (2019)
		- Biogas production	Mancini <i>et al.</i> (2016)
		- Biogas production	Ward-Doria <i>et al.</i> (2016)
		- Biobutanol production	Sandesh <i>et al.</i> (2020)
		- Biogas	Dahunsi <i>et al.</i> (2019b)

Ofori-Boateng and Lee (2013) evaluated CPH as a solid base catalyst for the transesterification of soy oil into biodiesel. According to their results, CPH potash could be a viable basic catalyst, generate high yields in biodiesel production, and offer engine

performance similar to that of petroleum diesel. Table 5 summarizes the routes for converting CPH into bioproducts for valorization.

Anaerobic digestion is a natural process that occurs in an oxygen-free environment (Morales *et al.* 2019). During this process, biodegradable materials are converted into biogas using microorganisms (Morales *et al.* 2019). Several studies have shown the application of this process to convert CPH to produce biogas (Ward-Doria *et al.* 2016) after alkaline and acid pretreatment. In addition, the use of response surface methodology to assess the effect of hydrothermal pretreatment on biogas yield and optimal pretreatment conditions was examined by Antwi *et al.* (2019). In addition, Acosta *et al.* (2018) demonstrated the potential of cocoa waste as a renewable energy source in rural areas *via* anaerobic digestion.

Artificial neural networks have also been used to predict biodigester production using CPH as biomass at the University of Piura pilot plant in Peru (Morales *et al.* 2019). Further, the co-digestion of biomass residues to produce fuel has also been presented in recent studies, in which biogas was produced from CPH and poultry manure (Dahunsi *et al.* 2019b).

Cocoa pod husks have also been explored commercially and industrially through patent research and development to take advantage of their rich chemical and biochemical compositions (Vásquez *et al.* 2019). Previous studies have shown the potential applications of CPH (Vásquez *et al.* 2019). Therefore, CPH is widely used because it allows the implementation of new products with high added value by using new processes that are applicable to the food, cosmetic, pharmaceutical, and biomaterial industries (Vásquez *et al.* 2019). Table 6 presents a brief list of product patents related to the use of CPH.

Table 6. Patents Related to the Use of Cocoa Pod Husk

Patent Number	Use	Reference
US4206245A	Preparation of small animal feed from CPH	Drevici and Drevici (1980)
WO2014042517A2	Biofertilizer	Rahman <i>et al.</i> (2014)
WO2015018957A1	Method for the synthesis of active carbon monoliths from cacao skin	Monge (2015)
ES2539845B1	Procedure and synthesis of activated carbon monoliths from cocoa pod husk	Monge (2016)
EP3613297A1	Procedure for extracting pectin from CPH and application in the food, pharmaceutical and personal care industries	Bernaert (2020)
WO2020038906A1	Cacao pod husk powder, method of its preparation and its use in food, pharmaceutical and cosmetic compositions	Bernaert and Kopp (2020a)
WO2020038905A1	Process to extract components of cacao pod husks and to utilize cacao fruit soluble extract obtained thereof and its applications	Bernaert and Kopp (2020b)

In the following sections, the current state of the valorization of CPH and its potential applications are described.

Valorization of Cocoa Pod Husk Residues into High Value-added Products

Soap making

Consumers are becoming more conscious of natural and organic personal care products, as certain synthetic chemicals have been shown to be harmful to humans (Gyedu-Akoto *et al.* 2015). Cocoa pods husks, which make up 60% to 75% of the cocoa fruit, contain a large amount of minerals, the most abundant of which is potassium (K); thus, this residue is an inexpensive source of caustic potash (Gyedu-Akoto *et al.* 2015). Cocoa pod husks could therefore be used for soap making in West African countries (Gyedu-Akoto *et al.* 2015). Indeed, each tonne of pods would produce approximately 6 kg of potash (Gyedu-Akoto *et al.* 2015). After filtering and concentration, this potash could be used for the saponification of oil to produce soap (Onyegbado *et al.* 2002). Some soaps derived from CPH have been successfully produced in a pilot plant in Ghana and in several African countries (Gyedu-Akoto *et al.* 2015). Potash-based soaps from CPH have higher solubility, consistency, cleaning power, and foaming capacity than chemical KOH-based soaps (Taiwo and Osinowo 2001). Appropriate use as a raw material for making commercial soap could also generate additional income for farmers in cocoa-producing countries.

Extracting bioactive compounds

The increasingly strong demand for crude oil reserves and the intensification of the effect of greenhouse gases are prompting researchers to implement chemical production processes based on biomass instead of petrochemical processes (Mansur *et al.* 2014). Lignocellulosic biomass is an accessible, renewable, and abundant resource. It is considered the only raw material for the sustainable production of platform chemicals (Mansur *et al.* 2014).

Lignocellulosic biomass has been increasingly used for the production of platform chemicals (Mansur *et al.* 2014). Among these chemicals with high added value, pectin, which is a natural food hydrocolloid, has use in the food industry for its gelling properties (Priyangini *et al.* 2018). Cocoa pod husks, which are a residual and abundant biomass, are part of the crop waste that can be used for this purpose (Vriesmann *et al.* 2011a; Mansur *et al.* 2014). The composition of CPH, the main waste product of cocoa production, and some of the characteristics of their hot-water-soluble pectins have been determined (Vriesmann *et al.* 2011a). The authors have shown that water, a natural extraction agent, could be used to obtain pectins more effectively than a conventional extraction based on mineral acids (Vriesmann *et al.* 2011a) because there was no pectin formation. This study demonstrates that cocoa pod husks have a high content of dietary fiber and phenolic compounds (Vriesmann *et al.* 2011a), which makes them a potential source of natural compounds with exceptional nutritional and functional qualities. The variables that influence the nitric acid extraction of pectins from cocoa pods husks were examined by Vriesmann *et al.* (2011b). The authors used a central-composite design based on the response surface methodology with three factors, which were hydrogen potential (pH), extraction temperature (T), and extraction time (t) (Vriesmann *et al.* 2011b). Cocoa pod husks were used by Priyangini *et al.* (2018) as a source for extracting pectin by treatment with sweet acid (ascorbic acid). A comprehensive factorial design was applied by these authors to examine the independent variables that affect yield and uronic acid content (Priyangini *et al.* 2018). A Box-Behnken design was used to optimize the supercritical CO₂ (SC-CO₂) extraction to develop an appropriate ecological process aimed to obtain an extract enriched in phenolic compounds from the pods of CPH (Valadez-Carmona *et al.* 2018). This process made it possible to reduce the extraction times (with low yield), to improve the quality of the extracts, and to reduce the loss of volatile compounds (Valadez-Carmona *et al.* 2018). In addition, it avoided the degradation of bio-compounds due to heat and reduced the high solvent

consumption (Valadez-Carmona *et al.* 2018). The results of the study showed that supercritical fluid extraction could be used as a technique to obtain an extract enriched in phenolic compounds from CPH (Valadez-Carmona *et al.* 2018). Abdul Karim *et al.* (2014a) performed a study to determine the total phenolic and flavonoid content of CPH compared to cocoa bean shell. They determined that CPH and cocoa bean shell have antioxidant activity with promising amounts of total phenolic and flavonoid content (Abdul Karim *et al.* 2014b).

Therefore, CPH are agricultural residues of great importance and can be used as basic raw materials for the synthesis of useful products in cosmetics (Abdul Karim *et al.* 2016). The highly active and stable crosslinked enzyme aggregate (CLEA)-lipase from the pod husks has been tested for its hydrolytic activity and successfully characterized under optimal conditions (Khanahmadi *et al.* 2015). The core-composite design based on response surface methodology was used to achieve the optimal conditions for pectin extraction (Vriesmann and de Oliveira Petkowicz 2017). Pectin was extracted from cocoa pod husks using aqueous nitric acid as an extractant and boiling water (Vriesmann and de Oliveira Petkowicz 2017). This study showed that pectin from the CPH could form low pH gels with reduced water activity (Vriesmann and de Oliveira Petkowicz 2017). This discovery encourages further work on the application of pectins obtained in acidic products from CPH (Vriesmann and de Oliveira Petkowicz 2017). Mansur *et al.* (2014) treated CPH by pyrolysis to produce a pyrolysis oil that contained several chemical compounds, such as ketones, carboxylic acids, aldehydes, furans, heterocyclic aromatics, alkylbenzenes, phenols, and benzenediols (Vriesmann and de Oliveira Petkowicz 2017). The authors obtained an improved pyrolysis oil compared to that obtained from iron oxide catalysts.

Hernández-Hernández *et al.* (2019) have implemented industrial technologies, such as heat treatment between 50 °C and 200 °C, which are currently used for the use and recovery of other lignocellulosic by-products. This allowed the extraction of bioactive compounds from CPH of several Mexican genotypes (Hernández-Hernández *et al.* 2018). Hydrothermal treatments at 150 °C or higher increased the solubilization of bioactive compounds and the antioxidant activity of the liquid phase (Hernández-Hernández *et al.* 2018). Treatment at 170 °C with water for 30 min was the most effective temperature for extracting both phenolics and sugars (Hernández-Hernández *et al.* 2018). However, 200 °C for 5 min was the best temperature for extracting theobromine and catechin (Hernández-Hernández *et al.* 2018).

Cocoa pod husk oil was studied by Adewole *et al.* (2015) to reveal the various compounds that it contained. Essential fatty acids and other organic compounds were revealed *via* a mass spectrophotometer coupled with gas chromatography. Further, low molecular weight carboxylic acids with a high yield were obtained by Asiedu *et al.* (2019) *via* an oxidation method catalyzed by two catalysts supported by metals that used CPH as the renewable material. The profiles of the concentration-time curves enabled the authors to model the kinetics and use the results to develop a new industrial operating technique, namely the concept of accessible region (AR) (Asiedu *et al.* 2019). This technique made it possible to minimize the volume of the reactors (thereby of the mass of catalyst) and to maximize the yield using a geometric optimization approach. In addition, Uy *et al.* (2019) found that CPH could be effectively converted to furfural. The authors also noted that a relatively high furfural yield (460.7 ppm) was achieved using an experimental Box-Behnken model to obtain the optimal conditions for the extraction of crude furfural by acid catalysis (Uy *et al.* 2019).

The phytochemicals of CPH have been extracted (Rachmawaty *et al.* 2018). Their phenolic content and the bioactivity of a CPH extract against the pathogenic fungus *Fusarium oxysporum* were tested. Antifungal tests *via* the agar diffusion method revealed that an extract of CPH with acetone was capable of inhibiting the growth of *Fusarium oxysporum* (pathogen of the fungus on tomatoes) (Rachmawaty *et al.* 2018).

Organic composts

Depletion of fertile soils due to lack of nutrients is a concern in tropical regions (Fidelis and Rao 2017). Composting can potentially recycle waste to conserve natural resources. The high mineral content of cocoa pod husks (CPH) or cocoa pod biomass (CPB), mainly in potassium (K), calcium (Ca), and phosphorus (P), suggests a potential to partially replace conventional fertilizers. Cocoa pod husks have been used as an organic amendment to fertilize degraded and ferralitic soils in the Oumé cocoa zone in Ivory Coast (Djeke *et al.* 2011). Cocoa pod husks are a source of organic matter that can improve the chemical parameters of soil and, under certain conditions, they could be used to fertilize degraded ferralitic soils in the Oumé region. The sorption and desorption of phosphate-P, ammoniacal nitrogen, and nitrate-N in biochars from cocoa pods husks and maize cobs were studied by Hale *et al.* (2013). They showed that biochar can slowly add and release essential nutrients to the soil to improve soil properties.

Another study by Munongo *et al.* (2017) produced compost manure and biochar from cocoa pods husks. Similarly, Ibiremo and Akanbi (2015) evaluated the effect of using a biochar enriched with different formulations of NPK fertilizers (solids and liquids) on CPH on the absorption of nutrients by kola seedlings and soil properties. Biochar and compost have been found to be alkaline in nature, which makes them suitable as a soil amendment, especially in acidic tropical soils.

The compost potential of CPH was evaluated by Doungous *et al.* (2018) as a soil conditioner to reduce the severity of black pod rot and consequently promote plant growth. Their results showed that the compost application increased soil pH and majority of the essential elements but decreased Al content, which is toxic to cocoa growth in acidic soils (Doungous *et al.* 2018). Further, Fidelis and Rao (2017) examined the possibility of producing nutrient-enriched compost from CPH that was infested with parasites with chemical amendments. When composted with superphosphate and poultry manure, CPH have produced good quality composts (Fidelis and Rao 2017). Such environmentally friendly applications could potentially reduce the use of expensive NPK fertilizers (Lu *et al.* 2018).

Activated carbon precursor

In general, 10 tonnes of CPH are yielded in the production of 1 tonne of dry beans (Pua *et al.* 2013). Based on its lignocellulosic content (Tsai and Huang 2018) and its abundant quantity, CPH appears to be an excellent precursor of activated carbon (AC). In fact, CHP, which is abundantly produced in certain African and Asian countries, has been tested as a precursor of AC to give it added value and avoid serious environmental problems linked to its presence in production fields.

Several works have mentioned its use. According to Cruz *et al.* (2012) CPH contains three chemical activating agents (K_2CO_3 , KOH, and $ZnCl_2$) that allow activated carbon to be obtained from them. The results obtained revealed that CPH can be used to produce AC by chemical activation (Cruz *et al.* 2012). In Nigeria, CPH have been used to adsorb heavy metals (Pb and Cu) from effluent water (Odubiyi *et al.* 2012). The resulting

products were tested to adsorb heavy metals in effluent water at variable pH levels, dosages, and contact times. The effects of physical activation by carbon dioxide (CO₂) on the porosity and surface functional groups of AC prepared from the cocoa pod husks were evaluated (Ahmad *et al.* 2013b). In addition, the effects of acid leaching from CPH have been reported (Ahmad *et al.* 2013a). The study focused on porosity and surface functional groups (Ahmad *et al.* 2013a). Cocoa pod husks have also been used as an adsorbent to remove methylene blue (MB) from aqueous solutions (Pua *et al.* 2013). Pereira *et al.* (2014) conducted a study on the recovery of two agricultural residues. Their work aimed to prepare AC from CPH and siriguela seeds and to assess the adsorption of whey proteins (Bovine Serum Albumin (BSA)) and α -bactalbumin on the AC produced. Moreover, AC was synthesized and then characterized at low temperature from CPH that were modified with zinc chloride (ZnCl₂) to eliminate amoxicillin (Tejada *et al.* 2017). The biomass was characterized by elemental analysis, and the AC obtained was analyzed by scanning electron microscopy (SEM) and X-ray diffraction (XRD), followed by Brunauer-Emmett-Teller (BET) surface analysis (S_{BET}) to determine its chemical composition and its morphological and structural characteristics. The proximal analysis performed on the biomass (CPH) showed a high carbon content, which makes it a suitable raw material for AC synthesis. In addition, Tsai *et al.* (2017) focused on the thermochemical characterization of biochar on CPH prepared at low pyrolysis temperature.

The results obtained by Tsai *et al.* (2017) highlighted the thermochemical characteristics of CPH to provide basic information on the thermochemical properties of CPH-based biochars. The results of the thermochemical characterization, which included analyses of the calorific value and mineral components of CPH, showed the presence of a percentage of volatile matter and a calorific value greater than 17.8 MJ/kg, but there was a high K content in the ash (4.03 wt%) (Tsai *et al.* 2017). Cocoa residues were also used by Tovar *et al.* (2018) to produce AC at low pyrolysis temperature. The authors prepared and characterized the biochar by SEM analysis (Tovar *et al.* 2018). They determined the chemical composition of the CPH and evaluated its use as a precursor of AC to eliminate amoxicillin and ibuprofen (Tovar *et al.* 2018). Another study proposed a strategy to modify the chemical properties of CPH to provide additional value (Fioresi *et al.* 2017). The authors stated that the grafting of aryl diazonium salt on CPH is spontaneous (Fioresi *et al.* 2017). They also elucidated that lignin was mainly involved in the immobilization of the phenolic layer (Fioresi *et al.* 2017). A study by Tsai and Huang (2018) improved the adsorption capacity of AC from ground CPH, and the authors reused the solution as a liquid fertilizer after acid leaching. The effectiveness of pyrolysis techniques for the heat treatment of CPH has been demonstrated from the thermochemical conversion and characterization of CPH (Adjin-Tetteh *et al.* 2018; Tsai *et al.* 2020). The authors used rapid pyrolysis technologies that had notable advantages over other biomass- and waste-treatment technologies.

Raw material for catalyst synthesis

Biodiesel production is typically achieved through the process of transesterification (Abdullah *et al.* 2017). Indeed, this process is one of the simplest and most beneficial for producing biodiesel (Abdullah *et al.* 2017). It is catalyzed by a suitable heterogeneous or homogeneous catalyst (Abdullah *et al.* 2017). The use of lipases as a transesterification catalyst in reactions involving enzymes can be an excellent alternative to the production of environmentally friendly biodiesel (Khanahmadi *et al.* 2016). In this context, the transesterification of *Jatropha curcas* oil was enhanced using the enzyme aggregate-

crosslinked lipase (CLEA) that was extracted from CPH (Khanahmadi *et al.* 2016). Further, it has been shown that it is possible to produce heterogeneous green basic catalysts from CPH to sustainably produce biodiesel (Ofori-Boateng and Lee 2013).

This type of catalyst offers several advantages, in that it is renewable, non-toxic, and reusable (Abdullah *et al.* 2017). In addition, it has high catalytic activity, stability in acidic and basic conditions, and high tolerance to water (Abdullah *et al.* 2017). Abdullah *et al.* (2017) examined the development of a heterogeneous base and an acid catalyst derived from biomass to produce biodiesel. A biodiesel conversion rate of up to 85% was achieved, and the results of the study showed that the biodiesel produced complied with standard SNI 7182: 2015 (2017)

After the pretreatment of cooking oil to reduce free fatty acids, a comparison of the efficiency of catalysts based on chicken eggshells and CPH was carried out for the production of biodiesel by transesterification (Andherson *et al.* 2018). The authors obtained 81.4% conversion of biodiesel with the chicken eggshell catalyst (CaO) and obtained approximately 85% conversion of biodiesel with the reaction that used K_2CO_3 obtained from the cocoa pod husks (Andherson *et al.* 2018). Indeed, the use of heterogeneous catalysts from biomass to produce biodiesel seems to be a promising choice, as it eliminates the tedious tasks and problems of homogenous operations (Abdullah *et al.* 2017). However, more research on catalysts from cocoa residues is needed to improve the catalytic performance of biodiesel production and other chemical processes (Abdullah *et al.* 2017).

Producing animal feed

Recent studies have focused on the growth of pigs (Balentić *et al.* 2018). Magistrelli *et al.* (2016) showed that the use of CPH in pig feed can have a positive effect on the balance of the intestinal microbial ecosystem (Magistrelli *et al.* 2016). These studies were confirmed after analyzing the addition of 20% CPH to pig feed (Ogunsipe *et al.* 2017). The authors showed that this rate was the optimal biological level for the use of CPH as an energy substitute for maize in pig feed (Ogunsipe *et al.* 2017). All of these studies demonstrate that CPH have a high potential for use as livestock feed to replace expensive conventional food ingredients.

Bioenergies and biofuels

The problems related to the use of fossil fuels require a transition to renewable energy sources (Chan and Choo 2013). Currently, the replacement of fossil fuels with renewable energies is increasing worldwide (Morato *et al.* 2019). The use of renewable resources and clean technologies remains a challenge for developing countries (Morato *et al.* 2019). Given the growing demand for energy, the search for other sources of energy production that are cheap, ecological, renewable, and suitable to replace fossil fuels is underway. Chan and Choo (2013) focused on the pyrolytic conversion of CPH in an electric thermal reactor of the fixed-bed type. The average calorific values of biofuel and biogas were improved compared to those obtained with other fuels, such as coal and ethanol (Chan and Choo 2013). However, Titiloye *et al.* (2013) showed that, during the thermochemical characterization of agricultural waste from West Africa, CPH would be better suited for biochemical conversion (Titiloye *et al.* 2013). This was confirmed by Mancini *et al.* (2016), as they showed that CPH have good potential for biogas production with accumulated methane yields. Likewise, Acosta *et al.* (2018) used CPH to produce methane. Their work consisted of evaluating the bioenergetic potential of CPH by anaerobic digestion (Acosta *et al.* 2018). Anaerobic digestion can stabilize organic matter and help retain nutrients

(Acosta *et al.* 2018). Further, it can increase the value of water for land applications and reduce potential negative impacts (Acosta *et al.* 2018). This study showed the potential of cocoa waste as a source of renewable energy in rural areas (Acosta *et al.* 2018). However, the structural and mechanical properties of cocoa waste hinder enzymatic and microbial degradation and impede the optimal production of biogas. To propose a solution to this difficulty, Ward-Doria *et al.* (2016) compared the effectiveness of acid (H₂SO₄) and alkaline (NaOH) pretreatments on CPH to increase the potential for biogas production by anaerobic digestion. Alkaline pretreatment had the best results in terms of reducing the lignin content. Shet *et al.* (2018a) performed hydrolysis with hydrochloric acid (HCl) to release reducing sugars from CPH (Shet *et al.* 2018a). These sugars were obtained under optimal conditions and subjected to alcoholic fermentation by *Pichia stipitis* to produce bioethanol (Shet *et al.* 2018a). Further, the thermal conversion of CPH was performed by Adjin-Tetteh *et al.* (2018) as a potential source of agricultural waste for the production of bio-oil *via* a rapid pyrolysis process. Thermogravimetric analysis indicated that CPH is an excellent raw material for pyrolysis (Adjin-Tetteh *et al.* 2018). To find an alternative to petroleum-based fuels and overcome the sharp fluctuation in market prices, Sandesh *et al.* (2020) conducted a comparative study of induction heating and liquefied petroleum gas (LPG) for acid hydrolysis from cocoa pod biomass (CPB). In their study (Sandesh *et al.* 2020), the optimization of the sulfuric acid pretreatment was preceded by a response surface methodology that studied the effect of the amount of acid used, the load of the biomass, and the time of stay in the reactor. Finally, an anaerobic acetone-butanol-ethanol (ABE) fermentation using *Clostridium acetobutanicum* MTCC11274 was carried out to produce biobutanol from optimized factors. The results showed that induction heating was more efficient than LPG heating.

Incorporating into food systems

The food industry has begun using more ingredients from natural sources, which is required by regulations and requested by consumers (Azila *et al.* 2014). Cocoa pods husks, which are used as a substrate to produce functional components in the food industry, offer the possibility of developing a new chain of products with high added value. Indeed, the rich composition in dietary fibers and antioxidants of CPH has been shown (Martínez-Ángel *et al.* 2015). Likewise, the nutritional quality of CPH was also evaluated by Kouakou *et al.* (2018) for plants and for humans. Analysis of the ash showed that CPH has a rich mineralogical composition (Kouakou *et al.* 2018). Cocoa pods husks could, therefore, contribute to the fight against hunger and malnutrition in cocoa-producing countries and be used as fertilizer for soils in rural areas. A study by Azila *et al.* (2014) demonstrated the utility of CPH as functional ingredients. In addition, CPH has great potential for use in body care products (Lu *et al.* 2018).

Use in paper industry

Much of global warming, soil erosion, and global climate change may be due to the large-scale deforestation of wood resources for the paper industry (Daud *et al.* 2013). Non-wood materials, such as CPH, are potential sources of fiber to produce pulp and paper (Daud *et al.* 2013). Daud *et al.* (2014) showed that the skin of CPH had a high lignocellulose content with linear fibrillar arrangements. This characteristic improves the resistance properties of the pulp and paper produced (Daud *et al.* 2014). In addition, chemical compositions and morphological surface studies indicated that CPH pulp is comparable to that of wood; thus, CPH would be a suitable pulp for use in paper

manufacturing industries (Daud *et al.* 2014). The authors conducted an additional study on the paper fibers of corn stalk and CPH (Daud *et al.* 2014). They showed an improved abundance of lignocellulosic substances from CPH and corn stalk, which could lead to improved fiber interfacial characteristics in papermaking.

Use as natural filler in the formulation of biocomposites

Recently, interest in the use of agricultural by-products as a natural filler in thermoplastic materials has arisen in research laboratories and industries (Chun *et al.* 2014b). Indeed, the use of natural fibers as reinforcement for composite materials can improve the properties or reduce the price of the final product. Efforts have been made by mixing and developing composites with other polymers and fillers (Helanto *et al.* 2019). In addition, composites based on natural fibers open up new outlets for agricultural products and promote the development of agro-materials and technologies that consider environmental impacts (Boudjema 2016). Natural fibers are valuable materials that have been produced and recycled naturally on earth for millions of years. They are biodegradable and renewable.

Cocoa pod husks are abundant in the Ivory Coast, as their annual production is estimated at over 50.25 billion pods (Kouakou *et al.* 2018). However, this biomass has no market value. In fact, CPH is typically thrown away as waste or composted to cultivate cocoa (Chun *et al.* 2014b). Using CPH as a reinforcing filler in biocomposites can generate economic benefits and reduce their ecological impact. However, the bonding strengths between agricultural waste reinforcements and polymer matrices are weak. Therefore, several strategies have been implemented to remedy this. Among them, the use of coupling agents to improve the charge-matrix interface and increase the thermo-mechanical properties of these biocomposites has been employed. In this context, the effect of the modification of the charge using methacrylic acid (MAA) on polypropylene composites (PP/CPH) was studied by Chun *et al.* (2013). These authors observed an increase in the stabilization torque, the crystallinity, and the thermal stability of PP/CPH composites. In addition, the strength and tensile modulus of the composites were improved (Koay *et al.* 2013). However, a reduction in elongation at break was observed. In another study, a biocomposite was developed by Chun *et al.* (2014b) from polypropylene and CPH to evaluate the effect of 3-aminopropyltriethoxysilane (3-APE) as a coupling agent in the treatment of CPH (Chun *et al.* 2014b). The treatment of CPH reduced the number of hydroxyl groups (-OH) on the surface, thus imparting hydrophobic properties to the filler and improving the charge-matrix interaction. The authors found a decrease in tensile strength and an increase in the tensile modulus with the addition of CPH and the treatment. This study also revealed that changes in filler content and processing have no influence on the melting temperature of biocomposites (Chun *et al.* 2014b).

Work has also focused on the use of CPH as a filler in PP biocomposites (Chun *et al.* 2015), and the thermal properties and morphologies of PP/CPH biocomposites were studied (Chun *et al.* 2015). The effect of different contents of palm oil-based coupling agent (POCA) on the tensile and morphological properties of polypropylene composites with different contents of CPH fillers was studied by Chun *et al.* (2014a). The results showed that 3% content of POCA gave the best tensile properties. Though the elongation at break decreased when the agent content was less than 3%, it began to increase beyond 3%. Further, SEM analysis showed better dispersion for the treated CPH and better adhesion with the PP matrix. Imoisili *et al.* (2013) studied the mechanical properties of CPH in a thermosetting polymer matrix (epoxy resin). The test results showed that the tensile and

flexural strength of the composite decreases as the volume fraction of the load decreases, and the tensile modulus of the composite increases as the volume fraction of the load increases (Imoisili 2013).

A Taguchi method approach was used to optimize the processing parameters of thermoplastic polyurethane (TPU) composites reinforced with CPH fibers (El-Shekeil *et al.* 2014b). The parameters were temperature, speed, processing time, and fiber content (El-Shekeil *et al.* 2014b). The ANOVA analysis results showed that fiber content was the most important parameter for producing TPU/CPHU (El-Shekeil *et al.* 2014b). After this optimization study, El-Shekeil *et al.* (2014a) analyzed the effect of CPH loading on the mechanical and morphological properties of TPU/CPH composites using the optimal parameters.

Battegazzore *et al.* (2014) proposed a simple method to separate three fractions of hazelnuts and CPH to use them as plasticizers for PLA and as load enhancers for PLA and PP. Application of the solution casting method to PLA composite films filled with CPH showed that increasing the CPH load from 0% to 10% significantly increased the tensile strength of the PLA/CPH composite (Sanyang *et al.* 2017). However, the further increase of CPH load to 15% decreased this resistance. Bioactive compounds extracted from CPH may have health benefits; therefore, they may be an alternative source of important components. Figure 9 summarizes the potential uses, current applications, and potential upgrades of CPH.

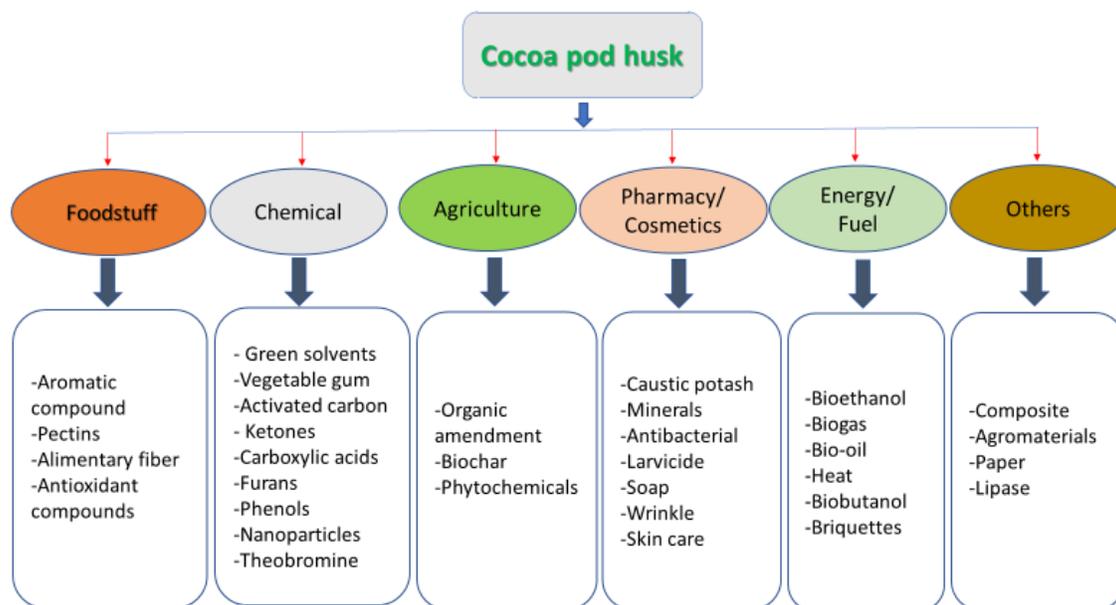


Fig. 9. Potential uses and applications of CPH

CONCLUSIONS

1. The chemical, physico-chemical, and biochemical characterization of the cocoa pod husks (CPH) has been carried out in numerous works. This step of the recovery process for this residue is crucial in order to understand the conversion processes. Indeed, it makes it possible to identify the most suitable recovery route and therefore the best uses of the material.

2. Several studies have reported the use of cocoa pods husks in many fields, such as animal feed, cosmetics, and biodegradable composites. However, applications related to biotechnology and the use of CPH as feed are still under study. Many studies have given added value to CPH by using them as a natural filler in polymer composite materials. Their use offers good biodegradability to the final product.
3. However, due to the recalcitrance of lignocellulose, optimal CPH pretreatment processes should be implemented to separate the main components at relatively low temperatures and (if possible) without the use of chemical agents. These processes are necessary to prevent the main components, namely lignocellulose components, pectin, and phenolic compounds, from losing their functionality. These components can have applications in food systems by offering improved nutritional value and can provide high yields of energy sources or chemicals for industry. Further, the present literature review on CPH residues has highlighted applications and products with a high commercial value.
4. However, no studies have been conducted using CPH as a natural filler in polylactic acid biopolymers to develop composite materials that have better thermomechanical and morphological properties, are green and fully biodegradable, and can replace conventional plastics from fossil resources. Consequently, the development of processes that are easy to implement, less expensive, sustainable, and green, is a necessity. This will transform cocoa waste into products with high added value and meet current and future challenges. The problems associated with poor cocoa waste management could be considerably reduced by the recovery and biotransformation of the molecular compounds available in CPH. Increased valorization of CPH will help to increase the overall sustainability of the cocoa agribusiness and open up a new source of income for cocoa farmers.

ACKNOWLEDGMENTS

The authors thank the International Development Research Center (IDRC) of Canada and the French Development Agency for their financial support.

CONFLICTS OF INTEREST

The authors declare that they have no conflict of interest.

REFERENCES CITED

- Abdul Karim, A., Azlan, A., Ismail, A., Hashim, P., Salwa, Gani, S. S. A., Zainudin, B. H., and Abdullah, N. A. (2014a). "Phenolic composition, antioxidant, anti-wrinkles and tyrosinase inhibitory activities of cocoa pod extract," *BMC Complementary and Alternative Medicine* 14, Article number 381. DOI: 10.1186/1472-6882-14-381
- Abdul Karim, A., Azlan, A., Ismail, A., Hashim, P., and Abdullah, N. A. (2014b). "Anti-oxidant properties of cocoa pods and shells," *Malaysian Cocoa Journal* 8, 49-56.

- Abdul Karim, A., Azlan, A., Ismail, A., Hashim, P., Gani, S. S. A., Zainudin, B. H., and Abdullah, N. A. (2016). "Efficacy of cocoa pod extract as antiwrinkle gel on human skin surface," *Journal of Cosmetic Dermatology* 15(3), 283-295. DOI: 10.1111/jocd.12218
- Abdullah, S. H. Y. S., Hanapi, N. H. M., Azid, A., Umar, R., Juahir, H., Khatoon, H., and Endut, A. (2017). "A review of biomass-derived heterogeneous catalyst for a sustainable biodiesel production," *Renewable and Sustainable Energy Reviews* 70, 1040-1051. DOI: 10.1016/j.rser.2016.12.008
- Acosta, N., de Vrieze, J., Sandoval, V., Sinche, D., Wierinck, I., and Rabaey, K. (2018). "Cocoa residues as viable biomass for renewable energy production through anaerobic digestion," *Bioresource Technology* 265, 568-572. DOI: 10.1016/j.biortech.2018.05.100
- Adewole, E., Ajiboye, B., Ojo, B., Ogunmodede, O. T., and Oso, O. (2015). "Characterization of cocoa (*Theobroma cacao*) pod," *International Journal of Scientific & Engineering Research* 4(1), 1-6.
- Adjin-Tetteh, M., Asiedu, N., Dodoo-Arhin, D., Karam, A., and Amaniampong, P. N. (2018). "Thermochemical conversion and characterization of cocoa pod husks a potential agricultural waste from Ghana," *Industrial Crops and Products* 119, 304-312. DOI: 10.1016/j.indcrop.2018.02.060
- Ahmad, F., Daud, W. M. A. W., Ahmad, M. A., and Radzi, R. (2013a). "The effects of acid leaching on porosity and surface functional groups of cocoa (*Theobroma cacao*)-shell based activated carbon," *Chemical Engineering Research and Design* 91(6), 1028-1038. DOI: 10.1016/j.cherd.2013.01.003
- Ahmad, F., Daud, W. M. A. W., Ahmad, M. A., Radzi, R., and Azmi, A. A. (2013b). "The effects of CO₂ activation, on porosity and surface functional groups of cocoa (*Theobroma cacao*)-shell based activated carbon," *Journal of Environmental Chemical Engineering* 1(3), 378-388. DOI: 10.1016/j.jece.2013.06.004
- Akinola, A. O., Eiche, J. F., Owolabi, P. O., and Elegbeleye, A. P. (2018). "Pyrolytic analysis of cocoa pod for biofuel production," *Nigerian Journal of Technology* 37(4), 1026-1031. DOI: 10.4314/njt.v37i4.23
- Alemawor, F., Dzagbefia, V. P., Oddoye, E. O. K., and Oldham, J. H. (2009). "Effect of *Pleurotus ostreatus* fermentation on cocoa pod husk composition: Influence of fermentation period and Mn²⁺ supplementation on the fermentation process," *African Journal of Biotechnology* 8(9), 1950-1958. DOI: 10.4314/ajb.v8i9.60454
- An, Y.-X., Zong, M.-H., Wu, H., and Li, N. (2015). "Pretreatment of lignocellulosic biomass with renewable cholinium ionic liquids: Biomass fractionation, enzymatic digestion and ionic liquid reuse," *Bioresource Technology* 192, 165-171. DOI: 10.1016/j.biortech.2015.05.064
- Andherson, T., Rachmat, D., and Risanti, D. D. (2018). "Potential use of chicken egg shells and cacao pod husk as catalyst for biodiesel production," *AIP Conference Proceedings* 1945(1), Article ID 020058. DOI: 10.1063/1.5030280
- Antwi, E., Engler, N., Nelles, M., and Schüch, A. (2019). "Anaerobic digestion and the effect of hydrothermal pretreatment on the biogas yield of cocoa pods," *Waste Management* 88, 131-140. DOI: 10.1016/j.wasman.2019.03.034
- Arevalo-Gallegos, A., Ahmad, Z., Asgher, M., Parra-Saldivar, R., and Iqbal, H. M. N. (2017). "Lignocellulose: A sustainable material to produce value-added products with a zero waste approach—A review," *International Journal of Biological Macromolecules* 99, 308-318. DOI: 10.1016/j.ijbiomac.2017.02.097

- Asiedu, N. Y., Neba, F. A., and Addo, A. (2019). "Modeling the attainable regions for catalytic oxidation of renewable biomass to specialty chemicals: Waste biomass to carboxylic acids," *South African Journal of Chemical Engineering* 30, 1-14. DOI: 10.1016/j.sajce.2019.07.003
- Aslanzadeh, S., Berg, A., Taherzadeh, M. J., and Horváth, S. I. (2014). "Biogas production from N-methylmorpholine-N-oxide (NMMO) pretreated forest residues," *Applied Biochemistry and Biotechnology* 172(6), 2998-3008. DOI: 10.1007/s12010-014-0747-z
- Babatope, B. (2005). "Rheology of cocoa-pod husk aqueous system. Part-I: Steady state flow behavior," *Rheologica Acta* 45(1), 72-76. DOI: 10.1007/s00397-005-0450-7
- Balentić, J. P., Ačkar, D., Jokić, S., Jozinović, A., Babić, J., Miličević, B., Šubarić, D., and Pavlović, N. (2018). "Cocoa shell: A by-product with great potential for wide application," *Molecules* 23(6), Article number 1404. DOI: 10.3390/molecules23061404
- Battegazzore, D., Bocchini, S., Alongi, J., and Frache, A. (2014). "Plasticizers, antioxidants and reinforcement fillers from hazelnut skin and cocoa by-products: Extraction and use in PLA and PP," *Polymer Degradation and Stability* 108, 297-306. DOI: 10.1016/j.polymdegradstab.2014.03.003
- Bernaert, H. (2020). "Procedure for extracting pectin from CPH and application in the food, pharmaceutical and personal care industries," European Patent No. EP3613297A1.
- Bernaert, H., and Kopp, G. (2020a). "Cacao pod husk powder, method of its preparation and its use in food, pharmaceutical and cosmetic compositions," World Intellectual Property Organization Patent No. WO2020038906A1.
- Bernaert, H., and Kopp, G. (2020b). "Process to extract components of cacao pod husks and to utilize cacao fruit soluble extract obtained thereof and its applications," World Intellectual Property Organization Patent No. WO2020038905A1.
- Beukes, N., and Pletschke, B. I. (2010). "Effect of lime pre-treatment on the synergistic hydrolysis of sugarcane bagasse by hemicellulases," *Bioresource Technology* 101(12), 4472-4478. DOI: 10.1016/j.biortech.2010.01.081
- Boudjema, H. L. (2016). *Development of Biodegradable Composite Materials Derived from Renewable Resources*, Ph.D. Dissertation, University of Oran 2 Mohamed Ben Ahmed, Bir El Djir, Algeria.
- Campos-Vega, R., Nieto-Figueroa, K. H., and Oomah, B. D. (2018). "Cocoa (*Theobroma cacao* L.) pod husk: Renewable source of bioactive compounds," *Trends in Food Science & Technology* 81, 172-184. DOI: 10.1016/j.tifs.2018.09.022
- Chan, S.-Y., and Choo, W.-S. (2013). "Effect of extraction conditions on the yield and chemical properties of pectin from cocoa husks," *Food Chemistry* 141(4), 3752-3758. DOI: 10.1016/j.foodchem.2013.06.097
- Chandra, R. P., Arantes, V., and Saddler, J. (2015). "Steam pretreatment of agricultural residues facilitates hemicellulose recovery while enhancing enzyme accessibility to cellulose," *Bioresource Technology* 118, 302-307. DOI: 10.1016/j.biortech.2015.02.106
- Chen, H., Liu, J., Chang, X., Chen, D., Xue, Y., Liu, P., Lin, H., and Han, S. (2017). "A review on the pretreatment of lignocellulose for high-value chemicals," *Fuel Processing Technology* 160, 196-206. DOI: 10.1016/j.fuproc.2016.12.007

- Chen, H.-Z., and Liu, Z.-H. (2015). "Steam explosion and its combinatorial pretreatment refining technology of plant biomass to bio-based products," *Biotechnology Journal* 10(6), 866-885. DOI: 10.1002/biot.201400705
- Cho, E. J., Trinh, L. T. P., Song, Y., Lee, Y. G., and Bae, H.-J. (2020). "Bioconversion of biomass waste into high value chemicals," *Bioresource Technology* 298, Article ID 122386. DOI: 10.1016/j.biortech.2019.122386
- Chun, K. S., and Husseinsyah, S. (2016). "Agrowaste-based composites from cocoa pod husk and polypropylene: Effect of filler content and chemical treatment," *Journal of Thermoplastic Composite Materials* 29(10), 1332-1351. DOI: 10.1177/0892705714563125
- Chun, K. S., Husseinsyah, S., and Osman, H. (2014a). "Preliminary study of palm oil based coupling agent for polypropylene/cocoa pod husk composites," *Advances in Environmental Biology* 8(8), 2640-2644.
- Chun, K. S., Husseinsyah, S., and Osman, H. (2014b). "Development of biocomposites from cocoa pod husk and polypropylene: Effect of filler content and 3-aminopropyl-triethoxysilane," *Polymers from Renewable Resources* 5(4), 139-156. DOI: 10.1177/204124791400500401
- Chun, K. S., Husseinsyah, S., and Osman, H. (2015). "Utilization of cocoa pod husk as filler in polypropylene biocomposites: Effect of maleated polypropylene," *Journal of Thermoplastic Composite Materials* 28(11), 1507-1521. DOI: 10.1177/0892705713513291
- Cruz, G., Pirilä, M., Huuhtanen, M., Carrión, L., Alvarenga, E., and Keiski, R. L. (2012). "Production of activated carbon from cocoa (*Theobroma cacao*) pod husk," *Journal of Civil & Environmental Engineering* 2(2), Article ID 1000109. DOI: 10.4172/2165-784X.1000109
- Dahunsi, S. O. (2019). "Mechanical pretreatment of lignocelluloses for enhanced biogas production: Methane yield prediction from biomass structural components," *Bioresource Technology* 280, 18-26. DOI: 10.1016/j.biortech.2019.02.006
- Dahunsi, S. O., Adesulu-Dahunsi, A. T., and Izebere, J. O. (2019a). "Cleaner energy through liquefaction of Cocoa (*Theobroma cacao*) pod husk: Pretreatment and process optimization," *Journal of Cleaner Production* 226, 578-588. DOI: 10.1016/j.jclepro.2019.04.112
- Dahunsi, S. O., Osueke, C. O., Olayanju, T. M. A., and Lawal, A. I. (2019b). "Co-digestion of *Theobroma cacao* (Cocoa) pod husk and poultry manure for energy generation: Effects of pretreatment methods," *Bioresource Technology* 283, 229-241. DOI: 10.1016/j.biortech.2019.03.093
- Daud, Z., Awang, H., Kassim, A. S. M., Hatta, M. Z. M., and Aripin, A. M. (2014). "Cocoa pod husk and corn stalk: Alternative paper fibres study on chemical characterization and morphological structures," *Advanced Materials Research* 911, 331-335. DOI: 10.4028/www.scientific.net/AMR.911.331
- Daud, Z., Kassim, A. S. M., Aripin, A. M., Awang, H., and Hatta, M. Z. M. (2013). "Chemical composition and morphological of cocoa pod husks and cassava peels for pulp and paper production," *Australian Journal of Basic and Applied Sciences* 7(9), 406-411.
- Djeke, M. D., Angui, P. K. T., and Kouadio, J. Y. (2011). "Décomposition des broyats de coques de cacao dans les sols ferrallitiques de la zone d'Oumé, centre-ouest de la Côte d'Ivoire : Effets sur les caractéristiques chimiques des sols [Decomposition of ground cocoa shells in ferrallitic soils in the Oumé zone, west-central Côte d'Ivoire:

- Effects on soil chemical characteristics],” *Biotechnology, Agronomy, Society and Environment* 15(1), 109-117.
- Dougous, O., Minyaka, E., Longue, E. A. M., and Nkengafac, N. J. (2018). “Potentials of cocoa pod husk-based compost on *Phytophthora* pod rot disease suppression, soil fertility, and *Theobroma cacao* L. growth,” *Environmental Science and Pollution Research International* 25(25), 25327-25335. DOI: 10.1007/s11356-018-2591-0
- Drevici, U., and Drevici, N. (1980). “Complete utilization of cocoa fruits and products,” U. S. Patent No. US4206245A.
- El-Shekeil, Y. A., Sapuan, S. M., and Algrafi, M. W. (2014a). “Effect of fiber loading on mechanical and morphological properties of cocoa pod husk fibers reinforced thermoplastic polyurethane composites,” *Materials & Design* 64, 330-333. DOI: 10.1016/j.matdes.2014.07.034
- El-Shekeil, Y. A., Sapuan, S. M., and Haron, M. (2014b). “Optimization of processing parameters and fiber content of cocoa pod husk fiber-reinforced thermoplastic polyurethane composites by Taguchi method,” *Applied Mechanics and Materials* 564, 394-399. DOI: 10.4028/www.scientific.net/AMM.564.394
- Fidelis, C., and Rao, B. K. R. (2017). “Enriched cocoa pod composts and their fertilizing effects on hybrid cocoa seedlings,” *International Journal of Recycling of Organic Waste in Agriculture* 6(2), 99-106. DOI: 10.1007/s40093-017-0156-8
- Fioresi, F., Vieillard, J., Bargougui, R., Bouazizi, N., Fotsing, P. N., Woumfo, E. D., Brun, N., Mofaddel, N., and Le Derf, F. (2017). “Chemical modification of the cocoa shell surface using diazonium salts,” *Journal of Colloid and Interface Science* 494, 92-97. DOI: 10.1016/j.jcis.2017.01.069
- Forero Nuñez, C. A., Jochum, J., and Sierra-Vargas, F. E. (2015). “Effect of particle size and addition of cocoa pod husk on the properties of sawdust and coal pellets,” *Ingeniería e Investigación* 35(1), 17-23. DOI: 10.15446/ing.investig.v35n1.46157
- Giwa, A. S., Ali, N., Vakili, M., Guo, X., Liu, D., and Wang, K. (2020). “Opportunities for holistic waste stream valorization from food waste treatment facilities: A review,” *Reviews in Chemical Engineering* 1(Preprint), Online. DOI: 10.1515/revce-2019-0064
- Gyedu-Akoto, E., Yabani, D., Sefa, J., and Owusu, D. (2015). “Natural skin-care products: The case of soap made from cocoa pod husk potash,” *Advances in Research* 4(6), 365-370. DOI: 10.9734/AIR/2015/17029
- Hale, S. E., Alling, V., Martinsen, V., Mulder, J., Breedveld, G. D., and Cornelissen, G. (2013). “The sorption and desorption of phosphate-P, ammonium-N and nitrate-N in cacao shell and corn cob biochars,” *Chemosphere* 91(11), 1612-1619. DOI: 10.1016/j.chemosphere.2012.12.057
- Helanto, K., Matikainen, L., Talja, R., and Rojas, O. J. (2019). “Bio-based polymers for sustainable packaging and biobarriers: A critical review,” *BioResources* 14(2), 4902-4951. DOI: 10.15376/biores.14.2.Helanto
- Hernández-Hernández, C., Morales-Sillero, A., Fernández-Bolaños, J., Bermúdez-Oria, A., Morales, A. A., and Rodríguez-Gutiérrez, G. (2019). “Cocoa bean husk: Industrial source of antioxidant phenolic extract,” *Journal of the Science of Food and Agriculture* 99(1), 325-333. DOI: 10.1002/jsfa.9191
- Hernández-Hernández, C., Viera-Alcaide, I., Morales-Sillero, A. M., Fernández-Bolaños, J., and Rodríguez-Gutiérrez, G. (2018). “Bioactive compounds in Mexican genotypes of cocoa cotyledon and husk,” *Food Chemistry* 240, 831-839. DOI: 10.1016/j.foodchem.2017.08.018

- Ibiremo, O. S., and Akanbi, O. S. O. (2015). "Comparative assessment of cocoa pod husk biochar fortified with NPK fertilizer formulations on kola seedling nutrient uptake and soil properties in Ibadan, Nigeria," *International Journal of Plant & Soil Science* 6(5), 303-309. DOI: 10.9734/IJPSS/2015/16111
- Imoisili, P. E., Ezenwafor, T. C., AttahDaniel, B. E., and Olusunle, S. O. O. (2013). "Mechanical properties of cocoa-pod/epoxy composite; Effect of filler fraction," *American Chemical Science Journal* 3(4), 526-531. DOI: 10.9734/ACSJ/2013/5526
- International Cocoa Organization (ICCO) (2019). "May 2019 quarterly bulletin of cocoa statistics," International Cocoa Organization (ICCO), (<https://www.icco.org/about-us/icco-news/408-may-2019-quarterly-bulletin-of-cocoa-statistics.html>), Accessed 10 Sept 2020.
- Jimat, D. Z., Salim, W. W. A. W., Avicenna, A., and Zailani, I. S. A. (2016). "Extraction of microcrystalline cellulose (MCC) from cocoa pod husk via alkaline pretreatment combined with ultrasonication," *International Journal of Applied Engineering Research* 11(19), 9876-9879.
- Khanahmadi, S., Yusof, F., Amid, A., Mahmud, S. S., and Mahat, M. K. (2015). "Optimized preparation and characterization of CLEA-lipase from cocoa pod husk," *Journal of Biotechnology* 202, 153-161. DOI: 10.1016/j.jbiotec.2014.11.015
- Khanahmadi, S., Yusof, F., Ong, H. C., Amid, A., and Shah, H. (2016). "Cocoa pod husk: A new source of CLEA-lipase for preparation of low-cost biodiesel: An optimized process," *Journal of Biotechnology* 231, 95-105. DOI: 10.1016/j.jbiotec.2016.05.015
- Kilama, G., Lating, P. O., Byaruhanga, J., and Biira, S. (2019). "Quantification and characterization of cocoa pod husks for electricity generation in Uganda," *Energy, Sustainability and Society* 9, Article number 22. DOI: 10.1186/s13705-019-0205-4
- Koay, S. C., Husseinayah, S., and Osman, H. (2013). "Modified cocoa pod husk-filled polypropylene composites by using methacrylic acid," *BioResources* 8(3), 3260-3275. DOI: 10.15376/biores.8.3.3260-3275
- Kouakou, E. K., Amed, C., Kouakou, F. K., Konan, C. M., Mouroufie, A. K., Kpan, E. S., Bouafou, K. G., and Kati-Coulibaly, S. (2018). "Cocoa pod in the Ivorian plantations: Green gold neglected and bulky?" *Nutrition & Food Science* 7(2), 1-3. DOI: 10.19080/NFSIJ.2018.07.555709
- Laconi, E. B., and Jayanegara, A. (2015). "Improving nutritional quality of cocoa pod (*Theobroma cacao*) through chemical and biological treatments for ruminant feeding: *In vitro* and *in vivo* evaluation," *Asian-Australasian Journal of Animal Sciences* 28(3), 343-350. DOI: 10.5713/ajas.13.0798
- Laser, M., Schulman, D., Allen, S. G., Lichwa, J., Antal, M. J., and Lynd, L. R. (2002). "A comparison of liquid hot water and steam pretreatments of sugar cane bagasse for bioconversion to ethanol," *Bioresource Technology* 81(1), 33-44. DOI: 10.1016/S0960-8524(01)00103-1
- Laurens, L. M. L., Nagle, N., Davis, R., Sweeney, N., Van Wychen, S., Lowell, A., and Pienkos, P. T. (2015). "Acid-catalyzed algal biomass pretreatment for integrated lipid and carbohydrate-based biofuels production," *Green Chemistry* 17(2), 1145-1158. DOI: 10.1039/C4GC01612B
- Lo, K. V., Srinivasan, A., Liao, P. H., and Bailey, S. (2015). "Microwave oxidation treatment of sewage sludge," *Journal of Environmental Science and Health, Part A* 50(8), 882-889. DOI: 10.1080/10934529.2015.1019811

- López-Linares, J. C., Ballesteros, I., Tourán, J., Cara, C., Castro, E., Ballesteros, M., and Romero, I. (2015). "Optimization of uncatalyzed steam explosion pretreatment of rapeseed straw for biofuel production," *Bioresource Technology* 190, 97-105. DOI: 10.1016/j.biortech.2015.04.066
- Lu, F., Rodriguez-Garcia, J., Van Damme, I., Westwood, N. J., Shaw, L., Robinson, J. S., Warren, G., Chatzifragkou, A., Mason, S. M., and Gomez, L., *et al.* (2018). "Valorisation strategies for cocoa pod husk and its fractions," *Current Opinion in Green and Sustainable Chemistry* 14, 80-88. DOI: 10.1016/j.cogsc.2018.07.007
- Maassen, S. (2016). "Bibliometric analysis of research on wastewater irrigation during 1991-2014," *Irrigation and Drainage* 65(5), 644-653. DOI: 10.1002/ird.1981
- Magistrelli, D., Zanchi, R., Malagutti, L., Galassi, G., Canzi, E., and Rosi, F. (2016). "Effects of cocoa husk feeding on the composition of swine intestinal microbiota," *Journal of Agricultural and Food Chemistry* 64(10), 2046-2052. DOI: 10.1021/acs.jafc.5b05732
- Maleka, D. (2016). *Assessment of the Implementation of Alternative Process Technologies for Rural Heat and Power Production from Cocoa Pod Husks*, Master's Thesis, KTH Royal Institute of Technology, Stockholm, Sweden.
- Mancini, G., Papirio, S., Lens, P. N. L., and Esposito, G. (2016). "Effect of N methylmorpholine-N-oxide pretreatment on biogas production from rice straw, cocoa shell, and hazelnut skin," *Environmental Engineering Science* 33(11), 843-850. DOI: 10.1089/ees.2016.0138
- Mansur, D., Tago, T., Masuda, T., and Abimanyu, H. (2014). "Conversion of cacao pod husks by pyrolysis and catalytic reaction to produce useful chemicals," *Biomass and Bioenergy* 66, 275-285. DOI: 10.1016/j.biombioe.2014.03.065
- Manzoor, Q., Nadeem, R., Iqbal, M., Saeed, R., and Ansari, T. M. (2013). "Organic acids pretreatment effect on *Rosa bourbonia* phyto-biomass for removal of Pb(II) and Cu(II) from aqueous media," *Bioresource Technology* 132, 446-452. DOI: 10.1016/j.biortech.2013.01.156
- Marsiglia, D. E., Ojeda, K. A., Ramirez, M. C., and Sánchez, E. (2016). "Pectin extraction from cocoa pod husk (*Theobroma cacao* L.) by hydrolysis with citric and acetic acid," *International Journal of Chemtech Research* 9(7), 497-507.
- Martínez-Ángel, J. D., Villamizar-Gallardo, R. A., and Ortíz-Rodríguez, O. O. (2015). "Characterization and evaluation of cocoa (*Theobroma cacao* L.) pod husk as a renewable energy source," *Agrociencia* 49(3), 329-345.
- Mirmohamadsadeghi, S., Chen, Z., and Wan, C. (2016). "Reducing biomass recalcitrance via mild sodium carbonate pretreatment," *Bioresource Technology* 209, 386-390. DOI: 10.1016/j.biortech.2016.02.096
- Monge, J. A. (2015). "Method for the synthesis of active carbon monoliths from cacao skin," World Intellectual Property Organization Patent No. WO 2015/018957 A1.
- Monge, J. A. (2016). "Procedure and synthesis of activated carbon monoliths from cocoa husk," Spanish Office of the Patents and Brand Patent No. ES 2 539 845 B1.
- Morales, L., Calderon, J., Solórzano, W., and Alvarado, I. (2019). "Modeling of cocoa pod husk anaerobic digester using artificial neural networks," in: *2019 IEEE XXVI International Conference on Electronics, Electrical Engineering and Computing (INTERCON)*, Lima, Peru, pp. 1-4.
- Morato, T., Vaezi, M., and Kumar, A. (2019). "Assessment of energy production potential from agricultural residues in Bolivia," *Renewable and Sustainable Energy Reviews* 102, 14-23. DOI: 10.1016/j.rser.2018.11.032

- Mosier, N., Hendrickson, R., Ho, N., Sedlak, M., and Ladisch, M. R. (2005). "Optimization of pH controlled liquid hot water pretreatment of corn stover," *Bioresource Technology* 96(18), 1986-1993. DOI: 10.1016/j.biortech.2005.01.013
- Munongo, M. E., Nkeng, G. E., and Njukeng, J. N. (2017). "Production and characterization of compost manure and biochar from cocoa pod husks," *International Journal of Advanced Scientific Research and Management* 2(2), 26-31.
- Nazir, N., Novelina, Juita, E., Amelia, C., and Fatli, R. (2016). "Optimization of pre-treatment process of cocoa pod husk using various chemical solvents," *International Journal on Advanced Science, Engineering and Information Technology* 6(3), 403-409. DOI: 10.18517/ijaseit.6.3.848
- Odubiyi, O. A., Awoyale, A. A., and Eloka-Eboka, A. C. (2012). "Wastewater treatment with activated charcoal produced from cocoa pod husk," *International Journal of Environment and Bioenergy* 4(3), 162-175.
- Ofori, P., and Akoto, O. (2020). "Production and characterisation of briquettes from carbonised cocoa pod husk and sawdust," *Open Access Library Journal* 7, e6029. DOI: 10.4236/oalib.1106029
- Ofori-Boateng, C., and Lee, K. T. (2013). "The potential of using cocoa pod husks as green solid base catalysts for the transesterification of soybean oil into biodiesel: Effects of biodiesel on engine performance," *Chemical Engineering Journal* 220, 395-401. DOI: 10.1016/j.cej.2013.01.046
- Ogunjobi, J. K., and Lajide, L. (2015). "The potential of cocoa pods and plantain peels as renewable sources in Nigeria," *International Journal of Green Energy* 12(4), 440-445. DOI: 10.1080/15435075.2013.848403
- Ogunsipe, M. H., Ibidapo, I., Oloruntola, O. D., and Agbede, J. O. (2017). "Growth performance of pigs on dietary cocoa bean shell meal," *Livestock Research for Rural Development* 29(1), 1-5.
- Onyegbado, C. O., Iyagba, E. T., and Offor, O. J. (2002). "Solid soap production using plantain peel ash as source of alkali," *Journal of Applied Sciences and Environmental Management* 6(1), 73-77. DOI: 10.4314/jasem.v6i1.17200
- Pereira, R. G., Veloso, C. M., da Silva, N. M., de Sousa, L. F., Bonomo, R. C. F., de Souza, A. O., da Guarda Souza, M. O., and da Costa Ilhéu Fontan, R. (2014). "Preparation of activated carbons from cocoa shells and siriguela seeds using H₃PO₄ and ZnCl₂ as activating agents for BSA and α -lactalbumin adsorption," *Fuel Processing Technology* 126, 476-486. DOI: 10.1016/j.fuproc.2014.06.001
- Priyangini, F., Walde, S. G., and Chidambaram, R. (2018). "Extraction optimization of pectin from cocoa pod husks (*Theobroma cacao* L.) with ascorbic acid using response surface methodology," *Carbohydrate Polymers* 202, 497-503. DOI: 10.1016/j.carbpol.2018.08.103
- Pua, F. L., Sajab, M. S., Chia, C. H., Zakaria, S., Rahman, I. A., and Salit, M. S. (2013). "Alkaline-treated cocoa pod husk as adsorbent for removing methylene blue from aqueous solutions," *Journal of Environmental Chemical Engineering* 1(3), 460-465. DOI: 10.1016/j.jece.2013.06.012
- Rachmawaty, Mu'nisa, A., Hasri, Pagarra, H., Hartati, and Maulana, Z. (2018). "Active compounds extraction of cocoa pod husk (*Theobroma cacao* L.) and potential as fungicides," in: *2nd International Conference on Statistics, Mathematics, Teaching, and Research*, Makassar, Indonesia, pp. 1-7.

- Rahman, R. N. Z. R. A., Salleh, A. B., Basri, M., and Samad, M. Y. A. (2014). "Biofertilizer," World Intellectual Property Organization Patent No. WO 2014/042517 A2.
- Rastegari, A. A., Yadav, A. N., and Gupta, A. (2019). *Prospects of Renewable Bioprocessing in Future Energy Systems*, Springer International Publishing, Cham, Switzerland.
- Rezania, S., Din, M. F., Mohamad, S. E., Sohaili, J., Taib, S. M., Yusof, M. B. M., Kamyab, H., Darajeh, N., and Ahsan, A. (2017). "Review on pretreatment methods and ethanol production from cellulosic water hyacinth," *BioResources* 12(1), 2108-2124. DOI: 10.15376/biores.12.1.Rezania
- Sandesh, K., Shishir, R. K., and Vaman Rao, C. (2020). "Optimization and comparison of induction heating and LPG assisted acid pretreatment of cocoa pod for ABE fermentation," *Fuel* 262, Article ID 116499. DOI: 10.1016/j.fuel.2019.116499
- Sanyang, M. L., Sapuan, S. M., and Haron, M. (2017). "Effect of cocoa pod husk filler loading on tensile properties of cocoa pod husk/polylactic acid green biocomposite films," *AIP Conference Proceedings* 1891(1), Article ID 020126. DOI: 10.1063/1.5005459
- Saratale, G. D., Jung, M.-Y., and Oh, M.-K. (2016). "Reutilization of green liquor chemicals for pretreatment of whole rice waste biomass and its application to 2,3-butanediol production," *Bioresource Technology* 205, 90-96. DOI: 10.1016/j.biortech.2016.01.028
- Shet, V. B., Nisha, Bhat, M., Manasa, Mascarenhas, L. N. S., Goveas, L. C., Rao, C. V., and Ujwal, P. (2016). "Optimization of Na₂CO₃ pre-treatment by RSM approach for releasing reducing sugars from cocoa pod shells," in: *Biotechnology and Biochemical Engineering*, B. D. Prasanna, N. G. Sathyanarayana, and P. V. Vadlani (eds.), Springer Singapore, East Singapore, Singapore, pp. 85-91.
- Shet, V. B., Sanil, N., Bhat, M., Naik, M., Mascarenhas, L. N., Goveas, L. C., Rao, C. V., Ujwal, P., Sandesh, K., and Aparna, A. (2018a). "Acid hydrolysis optimization of cocoa pod shell using response surface methodology approach toward ethanol production," *Agriculture and Natural Resources* 52(6), 581-587. DOI: 10.1016/j.anres.2018.11.022
- Shet, V. B., Shetty, V. C., Siddik, A., Rakshith, K. G., Shetty, N. J., Goveas, L. C., D'Mello, G., Rao, C. V., Ujwal, P., and Aparna, A. (2018b). "Optimization of microwave assisted H₂SO₄ hydrolysis of cocoa pod shells: Comparison between response surface methodology and artificial neural network and production of bioethanol thereof," *Journal of Microbiology, Biotechnology and Food Sciences* 7(5), 473-477. DOI: 10.15414/jmbfs.2018.7.5.473-477
- SNI 7182-2015 (2017). "Biodiesel specification in Indonesia," Indonesian Association of BioEnergy Scientists and Technologists, Pathumtani, Thailand.
- Statista (2019). "Cocoa beans: World production by country 2016-2019," Statista, (<https://fr.statista.com/statistiques/565101/production-mondiale-feves-cacao-volume-par-pays/>), Accessed 11 April 2020.
- Syamsiro, M., Saptoadi, H., Tambunan, B. H., and Pambudi, N. A. (2012). "A preliminary study on use of cocoa pod husk as a renewable source of energy in Indonesia," *Energy for Sustainable Development* 16(1), 74-77. DOI: 10.1016/j.esd.2011.10.005

- Taherzadeh, M. J., and Karimi, K. (2008). "Pretreatment of lignocellulosic wastes to improve ethanol and biogas production: A review," *International Journal of Molecular Sciences* 9(9), 1621-1651. DOI: 10.3390/ijms9091621
- Taiwo, O. E., and Osinowo, F. A. O. (2001). "Evaluation of various agro-wastes for traditional black soap production," *Bioresource Technology* 79(1), 95-97. DOI: 10.1016/S0960-8524(00)00188-7
- Tejada, C. N., Almanza, D., Villabona, A., Colpas, F., and Granados, C. (2017). "Characterization of activated carbon synthesized at low temperature from cocoa shell (*Theobroma cacao*) for adsorbing amoxicillin," *Ingeniería y Competitividad* 19(2), 45-54. DOI: 10.25100/iyc.v19i2.5292
- Thamsee, T., Choojit, S., Cheirsilp, B., Yamseangsung, R., Ruengpeerakul, T., and Sangwichien, C. (2019). "Combination of superheated steam explosion and alkaline autoclaving pretreatment for improvement of enzymatic digestibility of the oil palm tree residues as alternative sugar sources," *Waste and Biomass Valorization* 10(10), 3009-3023. DOI: 10.1007/s12649-018-0292-z
- Titiloye, J. O., Bakar, M. S. A., and Odetoeye, T. E. (2013). "Thermochemical characterisation of agricultural wastes from West Africa," *Industrial Crops and Products* 47, 199-203. DOI: 10.1016/j.indcrop.2013.03.011
- Tovar, C. T., Ortíz, A. V., Avila, A. C., Acevedo, D., and Gómez, N. P. (2018). "Kinetics and modelling of drug adsorption using activated carbon derived from cocoa cob waste," *International Journal of Chemtech Research* 11(5), 149-160. DOI: 10.20902/IJCTR.2018.110516
- Tsai, C.-H., Tsai, W.-T., Liu, S.-C., and Lin, Y.-Q. (2017). "Thermochemical characterization of biochar from cocoa pod husk prepared at low pyrolysis temperature," *Biomass Conversion and Biorefinery* 8, 237-243. DOI: 10.1007/s13399-017-0259-5
- Tsai, W.-T., and Huang, P.-C. (2018). "Characterization of acid-leaching cocoa pod husk (CPH) and its resulting activated carbon," *Biomass Conversion and Biorefinery* 8, 521-528. DOI: 10.1007/s13399-018-0302-1
- Tsai, W.-T., Hsu, C.-H., Lin, Y.-Q., Tsai, C.-H., Chen, W.-S., and Chang, Y.-T. (2020). "Enhancing the pore properties and adsorption performance of cocoa pod husk (CPH)-derived biochars via post-acid treatment," *Processes* 8(2), 144-157. DOI: 10.3390/pr8020144
- Umagiliyage, A. L., Choudhary, R., Liang, Y., Haddock, J., and Watson, D. G. (2015). "Laboratory scale optimization of alkali pretreatment for improving enzymatic hydrolysis of sweet sorghum bagasse," *Industrial Crops and Products* 74, 977-986. DOI: 10.1016/j.indcrop.2015.05.044
- Uy, J. R., Careo, N. D., Llarena, D., and Barajas, J. R. (2019). "Optimization of furfural extraction from *Theobroma cacao* wastes using response surface methodology," *MATEC Web of Conferences* 268, Article ID 06010. DOI: 10.1051/mateconf/201926806010
- Valadez-Carmona, L., Ortiz-Moreno, A., Ceballos-Reyes, G., Mendiola, J. A., and Ibáñez, E. (2018). "Valorization of cacao pod husk through supercritical fluid extraction of phenolic compounds," *The Journal of Supercritical Fluids* 131, 99-105. DOI: 10.1016/j.supflu.2017.09.011
- Vásquez, Z. S., de Carvalho Neto, D. P., Pereira, G. V. M., Vandenberghe, L. P. S., de Oliveira, P. Z., Tiburcio, P. B., Rogez, H. L. G., Neto, A. G., and Soccol, C. R.

- (2019). “Biotechnological approaches for cocoa waste management: A review,” *Waste Management* 90, 72-83. DOI: 10.1016/j.wasman.2019.04.030
- Vriesmann, L. C., de Mello Castanho Amboni, R. D., and de Oliveira Petkowicz, C. L. (2011a). “Cacao pod husks (*Theobroma cacao* L.): Composition and hot-water-soluble pectins,” *Industrial Crops and Products* 34(1), 1173-1181. DOI: 10.1016/j.indcrop.2011.04.004
- Vriesmann, L. C., and de Oliveira Petkowicz, C. L. (2017). “Cacao pod husks as a source of low-methoxyl, highly acetylated pectins able to gel in acidic media,” *International Journal of Biological Macromolecules* 101, 146-152. DOI: 10.1016/j.ijbiomac.2017.03.082
- Vriesmann, L. C., Teófilo, R. F., and de Oliveira Petkowicz, C. L. (2011b). “Optimization of nitric acid-mediated extraction of pectin from cacao pod husks (*Theobroma cacao* L.) using response surface methodology,” *Carbohydrate Polymers* 84(4), 1230-1236. DOI: 10.1016/j.carbpol.2011.01.009
- Wang, Y., Tashiro, Y., and Sonomoto, K. (2015). “Fermentative production of lactic acid from renewable materials: Recent achievements, prospects, and limits,” *Journal of Bioscience and Bioengineering* 119(1), 10-18. DOI: 10.1016/j.jbiosc.2014.06.003
- Ward-Doria, M., Arzuaga-Garrido, J., Ojeda, K. A., and Sánchez, E. (2016). “Production of biogas from acid and alkaline pretreated cocoa pod husk (*Theobroma cacao* L.),” *International Journal of Chemtech Research* 9(11), 252-260.
- Woiciechowski, A. L., Neto, C. J. D., de Souza Vandenberghe, L. P., de Carvalho Neto, D. P., Sydney, A. C. N., Letti, L. A. J., Karp, S. G., Torres, L. A. Z., and Soccol, C. R. (2020). “Lignocellulosic biomass: Acid and alkaline pretreatments and their effects on biomass recalcitrance – Conventional processing and recent advances,” *Bioresource Technology* 304, Article ID 122848. DOI: 10.1016/j.biortech.2020.122848
- Wyman, C. E., Dale, B. E., Elander, R. T., Holtzapple, M., Ladisch, M. R., and Lee, Y. Y. (2005). “Coordinated development of leading biomass pretreatment technologies,” *Bioresource Technology* 96(18), 1959-1966. DOI: 10.1016/j.biortech.2005.01.010

Article submitted: August 12, 2020; Peer review completed: October 18, 2020; Revised version received and accepted: October 27, 2020; Published: November 2, 2020.

DOI: 10.15376/biores.16.1.Ouattara